



# Standard Specification for Extended Life Type, Nonplowable, Prismatic, Raised, Retroreflective Pavement Markers<sup>1</sup>

This standard is issued under the fixed designation D 4280; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This specification covers nonplowable, retroreflective, raised pavement markers for lane marking and delineation for nighttime visibility.

1.2 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 The following precautionary caveat pertains only to the test methods portion, Section 9, of this specification: *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

### 2.1 ASTM Standards:

- C 184 Test Method for Fineness of Hydraulic Cement by the 150- $\mu\text{m}$  (No. 100) and 75- $\mu\text{m}$  (No. 200) Sieves<sup>2</sup>
- C 430 Test Method for Fineness of Hydraulic Cement by the 45- $\mu\text{m}$  (No. 325) Sieve<sup>2</sup>
- D 5 Test Method for Penetration of Bituminous Materials<sup>3</sup>
- D 36 Test Method for Softening Point of Bitumen (Ring-and-Ball Apparatus)<sup>4</sup>
- D 70 Test Method for Density of Semi-Solid Bituminous Materials (Pycnometer Method)<sup>3</sup>
- D 92 Test Method for Flash and Fire Points by Cleveland Open Cup<sup>5</sup>
- D 788 Classification System for Poly(Methyl Methacrylate) (PMMA) Molding and Extrusion Compounds<sup>6</sup>
- D 1754 Test Method for Effects of Heat and Air on Asphaltic Materials (Thin-Film Oven Test)<sup>3</sup>
- D 1856 Test Method for Recovery of Asphalt from Solution by Abson Method<sup>3</sup>
- D 2171 Test Method for Viscosity of Asphalts by Vacuum

### Capillary Viscometer<sup>3</sup>

- D 2172 Test Methods for Quantitative Extraction of Bitumen from Bituminous Paving Mixtures<sup>3</sup>
- D 2176 Test Method for Folding Endurance of Paper by the M.I.T. Tester<sup>7</sup>
- D 2669 Test Method for Apparent Viscosity of Petroleum Waxes Compounded with Additives (Hot Melts)<sup>8</sup>
- D 3935 Specification for Polycarbonate (PC) Unfilled and Reinforced Material<sup>9</sup>
- D 4402 Test Method for Viscosity Determinations of Unfilled Asphalts Using the Brookfield Thermoset Apparatus<sup>4</sup>
- D 5329 Test Methods for Sealants and Fillers, Hot-Applied, for Joints and Cracks in Asphaltic and Portland Cement Concrete Pavements<sup>3</sup>
- E 284 Terminology of Appearance<sup>10</sup>
- E 308 Practice for Computing the Colors of Objects by Using the CIE System<sup>10</sup>
- E 808 Practice for Describing Retroreflection<sup>10</sup>
- E 809 Practice for Measuring Photometric Characteristics of Retroreflectors<sup>10</sup>
- E 811 Practice for Measuring Colorimetric Characteristics of Retroreflectors Under Nighttime Conditions<sup>10</sup>
- 2.2 *Federal Specifications:*<sup>11</sup>
  - FF-W-1825A Wool and Gauze, Metallic
  - TT-T-291 Thinner, Paint, Mineral Spirits, Regular and Odorless
- 2.3 *AASHTO Standards:*<sup>12</sup>
  - AASHTO No. M237 Epoxy Resin Adhesive for Bonding Traffic Markers to Hardened Concrete
  - AASHTO No. T237 Testing Epoxy Resin Adhesive

## 3. Terminology

### 3.1 Definitions:

3.1.1 *coefficient of luminous intensity*,  $R_1$  (specific intensity)—the ratio of the luminous intensity ( $I$ ) of the retroreflector in the direction of observation to the illuminance ( $E$ ) at the retroreflector on a plane perpendicular to the

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee D04 on Road and Paving Materials and is the direct responsibility of Subcommittee D04.38 on Highway Traffic Materials.

Current edition approved Jan. 10, 2000. Published April 2000. Originally published as D 4280 – 83. Last previous edition D 4280 – 96.

<sup>2</sup> *Annual Book of ASTM Standards*, Vol 04.01.

<sup>3</sup> *Annual Book of ASTM Standards*, Vol 04.03.

<sup>4</sup> *Annual Book of ASTM Standards*, Vol 04.04.

<sup>5</sup> *Annual Book of ASTM Standards*, Vol 05.01.

<sup>6</sup> *Annual Book of ASTM Standards*, Vol 08.01.

<sup>7</sup> *Annual Book of ASTM Standards*, Vol 15.09.

<sup>8</sup> *Annual Book of ASTM Standards*, Vol 05.02.

<sup>9</sup> *Annual Book of ASTM Standards*, Vol 08.02.

<sup>10</sup> *Annual Book of ASTM Standards*, Vol 06.01.

<sup>11</sup> Available from U.S. Government Printing Office, Washington, DC 20402.

<sup>12</sup> Available from American Association of State Highway and Transportation Officials, 444 N. Capitol, Washington, DC 20001.

direction of the incident light, expressed in candelas per lux (cd/lx) (see Practice E 808 and Terminology E 284).

3.1.1.1 *Discussion*—When values are low the coefficient of (retroreflected) luminous intensity may be given in millicandelas per lux. In inch-pound units,  $R_I$  is given in candelas per footcandle (cd/ftc). Historically, the term specific intensity and symbol (SI) have been used to designate this term but  $R_I$  is preferred.

3.1.2 *color*—expressed by chromaticity coordinates according to the CIE (Commission Internationale de l’Eclairage 1931) standard colorimetric system.

3.1.3 *horizontal entrance angle*—the angle in the horizontal plane between the direction of incident light and the normal to the leading edge of the marker.

3.1.3.1 *Discussion*—This angle corresponds to the second component of the entrance angle  $\beta_2$ . The direction given in Practice E 808 should be used when designating this angle.

3.1.4 *observation angle*—the angle at the reflector between the illumination axis and the observation axis. (See also Practice E 808.)

3.1.5 *retroreflection*—reflection in which radiation is returned in directions close to the direction from which it came, this property being maintained over wide variations of the direction of incident radiation.

#### 4. Classification

4.1 Markers should be classified as to type, color, and surface characteristics.

##### 4.1.1 Types of Markers:

4.1.1.1 *Type A*—Two-way reflective markers, one color.

4.1.1.2 *Type B*—One-way reflective markers, one color.

4.1.1.3 *Type D*—One-way reflective markers, two colors (one-way reflective red with non-reflecting white surface on opposite side).

4.1.1.4 *Type E*—Two-way reflective markers, two colors.

##### 4.1.2 Color of Markers:

4.1.2.1 *W*—White.

4.1.2.2 *Y*—Yellow.

4.1.2.3 *R*—Red.

4.1.2.4 *B*—Blue.

4.1.2.5 *G*—Green.

##### 4.1.3 Surface Characteristics:

4.1.3.1 *No designation*—Marker with plastic lens surface.

4.1.3.2 *Designated H*—Marker with hard, abrasion-resistant lens surface.

4.2 Show classification in the order detailed in 4.1.1 through 4.1.3.2: type, color, and surface condition. For example, ERWH is a two-way red and white marker with abrasion resistant surface.

#### 5. Ordering Information

5.1 Orders for material under this specification should include the following information:

5.1.1 Quantity,

5.1.2 Type of marker: retroreflective one way, or retroreflective two way,

5.1.3 Color of marker, and

5.1.4 Surface condition, as-molded or abrasion resistant

#### 6. Requirements for Retroreflective Markers

##### 6.1 Construction:

6.1.1 Markers shall be of the prismatic reflector type.

6.1.2 The retroreflecting area shall be molded of methyl methacrylate material (see Classification D 788, Grade 8), impact modified methyl methacrylate (Classification D 788, see Note 1) or polycarbonate (Specification D 3935, Grade PC110B34750).

NOTE 1—A grade has not been stipulated because the committee responsible has not yet assigned a number.

6.1.3 Marker height shall not exceed 20.3 mm (0.80 in.).

6.1.4 Marker width shall not exceed 130 mm (5.1 in.).

6.1.5 The angle between the face of the marker and the base shall be no greater than 45°.

6.1.6 The base of the marker shall be substantially free from gloss or substances that may reduce its bond to adhesive.

6.1.7 The base of the marker shall be flat within 1.3 mm (0.05 in.). If the bottom of the marker is configured, the outermost faces of the configurations shall not deviate more than 1.3 mm (0.05 in.) from a flat surface.

6.1.8 Other construction meeting the performance requirements will be acceptable following a six-month road test during the time of the year when weather and traffic conditions are most critical to determine cleanability and durability.

##### 6.2 Performance Requirements:

6.2.1 For flat bottom markers, adhesive bond strength measured in accordance with 9.1 shall be not less than 3.4 MPa (500 psi). Flat bottom markers passing the 3.4 MPa (500 psi) requirement when tested with epoxy will be considered acceptable also for installation using bitumen as the adhesive. No suitable laboratory method for evaluating the adherence of configured-bottom (“waffle”-bottom) markers to either portland cement or asphalt roads has been developed.

6.2.2 Coefficient of luminous intensity measured in accordance with 9.2 shall be not less than the values in Table 1.

##### 6.2.3 Physical Properties:

6.2.3.1 *Flexural Strength* (for markers with length and width both equal to or greater than 4 in.)—Tested in accordance with 9.3.1, a marker shall withstand 909 kg (2000 lb)

**TABLE 1 Coefficient of Luminous Intensity  $R_I$**

NOTE 1—Entrance angle component  $\beta_1$  and rotation angle  $\epsilon$  are 0°.

Entrance Angle $\beta_2$	Observation Angle $\alpha$	Minimum Value $R_I$ , mcd/lx				
		White	Yellow	Red	Green	Blue
0°	0.2°	279	167	70	93	26
+ 20°/-20°	0.2°	112	67	28	37	10
Entrance Angle $\beta_2$	Observation Angle $\alpha$	Minimum Value $R_I$ , cd/ftc				
		White	Yellow	Red	Green	Blue
0°	0.2°	3.0	1.8	0.75	1.0	0.28
+ 20°/-20°	0.2°	1.2	0.72	0.30	0.4	0.11

without breakage or significant deformation. Significant deformation shall be understood to be 3.3 mm (0.13 in.).

6.2.3.2 *Compressive Strength* (for markers with length or width less than 4 in.)—Tested in accordance with 9.3.2, a marker shall support a load of 2727 kg (6000 lb) without breakage or significant deformation of the marker. Significant deformation shall be understood to be 3.3 mm (0.13 in.).

6.2.4 *Color*—When the retroreflector is illuminated by CIE Standard Source A and when measured in accordance with 9.4, the color of the retroreflected light shall fall within the color gamuts given by the following corner points and shown in Fig. 1.

6.2.4.1 *White*

Point No.	x	y
1	0.310	0.348
2	0.453	0.440
3	0.500	0.440
4	0.500	0.380
5	0.440	0.380
6	0.310	0.283

6.2.4.2 *Yellow*

Point No.	x	y
1	0.545	0.424
2	0.559	0.439
3	0.609	0.390
4	0.597	0.390

6.2.4.3 *Red*

Point No.	x	y
1	0.650	0.330
2	0.668	0.330
3	0.734	0.265
4	0.721	0.259

6.2.4.4 *Blue*

Point No.	x	y
1	0.039	0.320
2	0.160	0.320
3	0.160	0.240
4	0.183	0.218
5	0.088	0.142

6.2.4.5 *Green*

Point No.	x	y
1	0.009	0.733
2	0.288	0.520
3	0.209	0.395
4	0.012	0.494

6.2.5 *Resistance to Lens Cracking*—(abrasion resistant markers only).

6.2.5.1 *Lens Impact Strength*—When impacted in accordance with 9.5.1, the face of the lens shall show no more than two radial cracks longer than 6.4 mm (0.25 in.). There shall be no radial cracks extending to the edge of the abrasion resistant area. There shall be no delamination.

6.2.5.2 *Temperature Cycling*—When subjected to temperature cycling in accordance with 9.5.2 there shall be no cracking or delamination.

7. *Sampling*

7.1 For markers not resistant to abrasion, sample size shall be twenty markers for each lot of 10 000 markers or less and forty markers for each lot of more than 10 000 markers. For markers with an abrasion resistant surface, ten additional samples shall be required. Lot size shall not exceed 25 000 markers.

8. *Number of Tests and Retests*

8.1 For coefficient of luminous intensity (9.2.1), the entire sample of retroreflective pavement markers shall be tested. Failure of more than 10 % of the reflective faces shall be cause for rejection of the entire lot represented by the sample. For abrasion resistant markers, in addition to the test of 9.2.1 shall be subjected to abrasion (9.2.2) and remeasured; failure of more than one sample shall be cause for rejection of the entire lot.

8.2 For adhesive bond strength (9.1), flexural strength (9.3.1), compressive strength (9.3.2), and color (9.4) three specimens shall be tested. Specimens previously subjected to photometry (9.2.1), color (9.4) and the abrasion specified for 9.2.2 may be used for tests of adhesive bond strength (9.1), flexural strength (9.3.1) and compressive strength (9.3.2). Failure of more than one specimen shall be cause for rejection of the entire lot.

8.3 For abrasion resistant markers only, for lens impact strength (9.5.1) and resistance to temperature cycling (9.5.2), ten specimens shall be tested for each requirement. Failure of more than one of the specimens in either test shall be cause for rejection of the entire lot.

8.4 At the discretion of the engineer, a resample may be taken consisting of double the number of samples originally tested. Tolerances for resamples shall be in the same ratio as specified above.

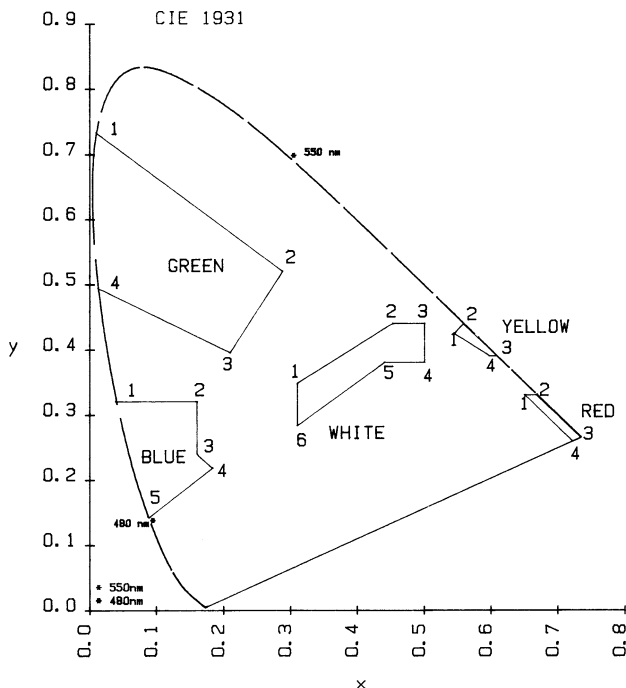


FIG. 1 Color Gamut per 6.2.4

9. Test Methods

9.1 Adhesive Bond Strength:

9.1.1 For markers with flat bottom, measure adhesive bond strength in accordance with Sections 12 and 13 of AASHTO No. T237, but substitute a pavement marker for the concrete block, and if the base of the marker is less than 50.8 mm (2.0 in.) in any direction, substitute a 25.4 mm (1.0 in.) diameter plug for the specified 50.8 mm (2.0 in.) plug. Position the pavement marker against a test plate having a hole through which the plug can be inserted and attached to a tensile member. No test has been developed for configurated-bottom markers to be applied with either bitumen or epoxy.

9.1.2 Conditioning temperature for components shall be  $23.0 \pm 2.0^{\circ}\text{C}$  ( $73.4 \pm 3.6^{\circ}\text{F}$ ).

9.1.3 Cure the assembly for 24 h at  $23.0 \pm 2.0^{\circ}\text{C}$  ( $73.4 \pm 3.6^{\circ}\text{F}$ ) before testing.

9.1.4 Rate of loading shall be 5.1 mm (0.2 in.)/min.

9.1.5 Adhesive used for test should conform to AASHTO No. M237, Type 1.

9.1.6 Source of Error:

9.1.6.1 Variation in thickness of epoxy has been found to influence test results,

9.1.6.2 Lack of parallelism of surfaces of test plug and marker can result in low readings, and

9.1.6.3 Variations in adhesive used for testing the marker will affect the test results.

9.1.7 Precision and Bias:

9.1.7.1 Since the test is destructive, correlation is affected by differences between test samples. Variations of 20 % within a given lot of markers may be expected.

9.1.7.2 No formal interlaboratory data on precision and bias are available. A correlation study to develop these data is planned.

9.2 Coefficient of Luminous Intensity:


9.2.1 Procedure—Measure coefficient of luminous intensity in accordance with Practice E 809 with high resolution aperture size per Table 1 of Practice E 809. Suggested dimensions are 30.5-m (100-ft) test distance, 25.4-mm (1.0-in.) diameter receptor and 25.4-mm (1.0-in.) diameter source. Other test distances 15.2 m (50 ft) and above may be used provided that the angular aperture requirements are met. Measure the distance from the light source exit pupil to the center of the retroreflective face of the marker. Place the base of the marker on a plane parallel to the illumination axis ( $\beta_1 = 0$ ) and perpendicular to the observation half-plane ( $\beta_2 = 0$ ). Refer to Fig. 2 and Practice E 809. The tolerance on entrance angle shall be  $\pm 0.5^{\circ}$  maximum.

9.2.2 For abrasion resistant markers, measure coefficient of luminous intensity after abrasion with a 25.4-mm (1-in.) diameter flat pad of No. 3 coarse steel wool conforming to Federal Specification FF-W-1825A. Place the steel wool pad on the reflector lens. Apply a load of  $22 \pm 0.2$  kg ( $50 \pm 0.5$  lb) and rub the entire lens surface 100 times.

NOTE 2—Some two-color units may intentionally have only one of the retroreflected faces covered with an abrasion-resistant surface and, if so, the unprotected face should not be abraded.

9.3 Physical Properties:

9.3.1 Flexural Strength:

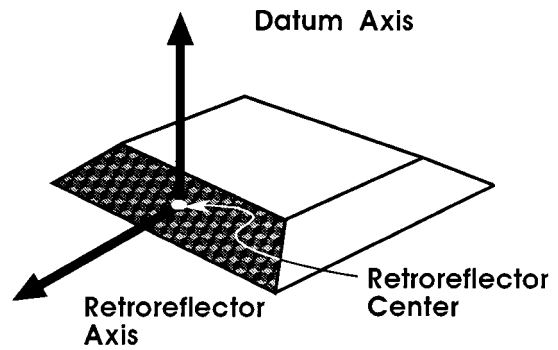

Location of retroreflector axis, datum axis and retroreflector center for use in testing raised pavement markers.

**Retroreflector Center**-located on the surface of the effective retroreflective area, centered both vertically and horizontally.

**Retroreflector Axis**-extends parallel to the road surface from retroreflector center.

**Datum Axis**-extends vertically from the road surface plane starting at retroreflector center.

FIG. 2 Position of Marker for Photometry

9.3.1.1 Condition markers at  $23.0^{\circ} \pm 2.0^{\circ}\text{C}$  ( $73.4^{\circ} \pm 3.6^{\circ}\text{F}$ ) for 4 h prior to testing.

9.3.1.2 Center marker base down over the open end of a vertically positioned hollow metal cylinder 25.4 mm (1.0 in.) high, with 76 mm (3 in.) inside diameter and 6.4 mm (0.25 in.) wall thickness.

9.3.1.3 Apply a load to the top of the marker at a rate of 5.0 mm (0.2 in.)/min through a 25.4 mm (1.0 in.) diameter metal plug centered on top of the marker.

9.3.2 Compressive Strength:

9.3.2.1 Condition markers at  $23.0 \pm 2.0^{\circ}\text{C}$  ( $73.4 \pm 3.6^{\circ}\text{F}$ ) for 4 h prior to testing.

9.3.2.2 Position marker base down at the center of a 13 mm (0.5 in.) thick flat steel plate larger than the marker.

9.3.2.3 On top of the marker place a 9.5 mm (0.37 in.) thick elastomeric pad larger than the marker and having a Shore A durometer of 60.

9.3.2.4 On top of the elastomeric pad place a 13 mm (0.5 in.) thick flat steel plate larger than the marker.

9.3.2.5 Apply a load at a rate of 2.5 mm (0.1 in.)/min.

9.4 Color—Measure color in accordance with Practice E 811 at  $0.2^{\circ}$  observation angle and  $0^{\circ}$  entrance angle. The source and receptor angular apertures shall each be 6 min of arc.

9.5 Resistance to Lens Cracking, hard surface markers only.

9.5.1 Lens Impact Strength—Condition the markers in a convection oven at  $55^{\circ}\text{C}$  ( $130^{\circ}\text{F}$ ) for 1 h.

9.5.1.1 While at the elevated temperature, impact the reflective face of the marker by allowing a 190-g (0.42-lb) dart fitted

with a 6.4-mm (0.25-in.) radius semi-spherical head to drop 457 mm (18 in.) perpendicularly onto the approximate center of the reflective surface. For impact testing, set the marker on a steel fixture designed to hold the reflecting face horizontal, and place the fixture on a solid surface such as a concrete floor.

9.5.1.2 Inspect for cracking and delamination.

9.5.2 *Resistance to Temperature Cycling*—Subject samples to 3 cycles of 60°C (140°F) for 4 h followed by – 7°C (20°F) for 4 h.

9.5.2.1 Inspect for cracking and delamination.

9.5.3 *Precision and Bias*—No statement is made about either the precision or bias of the test for resistance to lens cracking since the result merely states whether there is conformance the criteria for success specified in the procedure.

## 10. Packaging

10.1 Shipments shall be made in containers which are acceptable to common carriers and packaged in such a manner as to ensure delivery in perfect condition. Any damaged shipments shall be replaced by the contractor. Each package shall be clearly marked as to the name of the manufacturer, type, color, quantity enclosed, and date of manufacture.

## 11. Keywords

11.1 delamination; pavement markers; prismatic markers; raised pavement markers; retroreflective markers

## ANNEX

### (Mandatory Information)

#### A1. SPECIFICATION FOR BITUMINOUS ADHESIVE FOR PAVEMENT MARKERS

##### A1.1 Scope

A1.1.1 This specification establishes the requirements for bituminous installation adhesive to be used for placement of nonplowable, raised, retroreflective, pavement markers. The adhesive shall be suitable for bonding the above markers to portland cement concrete, asphaltic concrete, and chip sealed road surfaces and applicable when road surface and marker temperatures are in the range from 4.4 to 71°C (40 to 160°F). The adhesive properties will not deteriorate when heated to and applied at temperatures up to 218°C (425°F) using either air or oiljacketed melters.

##### A1.2 General Properties of Adhesive

A1.2.1 The bituminous installation adhesive is an asphaltic material with a homogeneously mixed mineral filler. The adhesive shall not contain rubber polymers since necessary application temperatures cause decomposition, resulting in unsatisfactory performance. The adhesive shall conform to the following requirements:

Property	Minimum	Maximum	Test Method
Softening point, °C (°F)	93 (200)	127 (260)	D 36
Penetration at 25°C, mm × 10 <sup>-1</sup>	10	18	D 5
Penetration at 60°C, mm × 10 <sup>-1</sup>	45	65	D 5 as in A1.4.8
Flow, mm (in.)	—	5.1 (0.2)	D 5329, as modified in A1.4.1
Heat stability flow, mm (in.)	—	5.1 (0.2)	As in A1.4.2
Viscosity at 204°C (400°F), P	30	75	D 2669, as modified in A1.4.3, or D4402
Flash point, C.O.C., °C (°F)	228 (550)	—	D 92
Shelf life, years	2	—	

##### A1.3 General Properties of Filler-Free Material and of Filler Alone

A1.3.1 Asphalt properties determined on the filler-free material derived from the extraction and Abson recovery process as explained in A1.4.4 are as follows:

Property	Minimum	Maximum	Test Method
Penetration, 100 g, 5s, 25°C (77°F)	25	—	D 5

Viscosity, 135°C (275°F), P	12	100	D 2171
Viscosity ratio, 135°C (275°F)	—	2.2	As explained in A1.4.5

A1.3.2 Filler properties determined using the filler separation technique described in A1.4.6.

Property	Minimum	Maximum	Test Method
Filler content, % by weight	65	75	As in A1.4.6
Filler fineness, % passing			
45-µm (No. 325) sieve	75	—	C 430
75-µm (No. 200) sieve	95	—	C 184
150-µm (No. 100) sieve	100	—	C 184

##### A1.4 Test Methods

A1.4.1 Determine flow in accordance with Section 6, Flow, of Test Methods D 5329 with the exception that the oven temperature shall be 70 ± 1°C (158 ± 2°F) and sample preparation shall be in accordance with Test Method D 5.

A1.4.2 Determine heat stability flow in accordance with Section 6 on Flow of Test Methods D 5329 with the exception that 1000 g of adhesive shall be placed in a covered quart can, heated to 218°C (425°F), and maintained at this temperature for 4 h prior to preparing the sample panel (6.1).

A1.4.3 Determine viscosity in accordance with Test Method D 2669 or D 4402. If using Test Method D 2669, use a spindle speed of 10 r/min, and heat the adhesive to approximately 210°C (410°F) and allow to cool; determine viscosity at 204.4 ± 0.5°C (400 ± 1°F). If using Test Method D 4402, the test method describes the spindle and speed to be used with various models.

A1.4.4 Determine properties of the base asphalt on the material obtained from the following extraction and Abson recovery methods. Extract the asphalt by heating the adhesive just to the point where it will easily flow and then transfer 125 to 150 g into 400 mL of trichloroethylene with a temperature of 52 to 65°C (125 to 150°F). Thoroughly stir this mixture to dissolve the asphalt. Decant the trichloroethylene-asphalt mixture and recover the asphalt using the Abson recovery method in accordance with Test Method D 1856 as modified by the



following. The extraction methods of Test Methods D 2172 shall not apply and there shall be no filtration of the solvent-asphalt mixture. Centrifuge the extraction solution of trichloroethylene and asphalt for at least 30 min at 770 times gravity in a batch centrifuge. A continuous centrifuge can be used if the extract solution is charged at a rate not to exceed 150 mL/min while the unit is operating at a speed calculated to produce a centrifuge force of not less than 3000 times gravity as specified in 9.2 of Test Method D 1856. Decant this solution into the distillation flask, taking care not to include any filler sediment. Apply heat and bubble carbon dioxide slowly to bring the solution temperature to 149°C (300°F). At this point, the carbon dioxide flow is increased to 800 to 900 mL/min. Maintain the solution temperature at 160 to 168°C (320 to 335°F) with this carbon dioxide flow rate for at least 20 min and until the trichloroethylene vapors have been completely removed from the distillation flask. Repeat the above extraction-recovery method as necessary to obtain the desired quantity of asphalt. Use the asphalt recovered to determine penetration, 135°C (275°F) viscosity, and 135°C (275°F) viscosity ratio.

A1.4.5 Determine the 135°C (275°F) viscosity ratio by comparing the 135°C (275°F) viscosity on the base asphalt before and after the Thin-Film Oven Test. Perform the Thin-Film Oven Test in accordance with Test Method D 1754. Determine the specific gravity by pycnometer in accordance with Test Method D 70 for use in the Thin-Film Oven Test. Calculate the 135°C (275°F) viscosity ratio by dividing the

viscosity after the Thin-Film Oven Test by the original 135°C (275°F) viscosity.

A1.4.6 To determine the filler content, use the data from the separation described in A1.4.4. The samples used for the asphalt recovery are weighed before the extractions. The extracted filler is weighed after extraction. The bitumen is determined by difference.

A1.4.7 Determine the fineness of the filler according to Test Method C 430 for material finer than the 45 µm (No. 325) sieve. Using a second test sample, determine the percentage of the material passing the 150 µm (No. 100) and 75 µm (No. 200) sieve according to Test Method C 184.

A1.4.8 Determine penetration at 60°C (140°F) in accordance with Section 8 of Test Method D 5 where the conditions of test are the following:

Temperature, °C (°F)	Load, g	Time, s
60 (140)	100	5

## A1.5 Packaging and Labeling

A1.5.1 The adhesive shall be packaged in self-releasing cardboard containers that will stack properly. The containers shall be divided into compartments so that four equal individual parts are obtained from each container. The containers shall have a net weight of approximately 25 kg (55 pd). The label for the container shall clearly show the manufacturer, quantity, lot or batch number, and an indication that the material is bituminous adhesive for pavement markers.

## APPENDIX

### (Nonmandatory Information)

#### X1. STORAGE, PLACEMENT AND APPLICATION OF NON-PLOWABLE MARKERS

X1.1 *Storage*—Markers should be stored indoors and should be protected from any source of moisture both during shipment to the jobsite and at the jobsite. The markers should be maintained at a high enough temperature as to preclude moisture condensation, and, at the time of placement, both the markers and their containers should be dry.

X1.2 *Placement of Non-plowable Markers*—Before beginning pavement marker application, the contractor should accurately and adequately lay out, by reference points, the location of all pavement markers, to ensure their proper placement. Pavement markers should not be placed on pavement surfaces that show visible evidence of cracking, checking, spalling, or failure of underlying base material. If, during the pre-installation layout operation, it is determined that a marker would be placed at a point with one of the aforementioned pavement surface defects or at a pavement construction joint or within the intersection of a driveway or public street as the result of typical marker spacing, the affected marker should be relocated longitudinally a sufficient distance to a point approved by the engineer. The distance the marker may be relocated should not exceed 10 % of the typical marker spacing. Where it would be necessary to relocate the marker a

distance greater than 10 % of the typical marker spacing, the affected marker should be deleted. The reflective face of the marker should be perpendicular to a line parallel to the roadway centerline.

X1.3 *Application of Non-plowable Markers*—Markers should be cemented to the pavement with Rapid Set Type adhesive conforming to the provisions of AASHTO No. M237, Type 1, or Standard Set Type adhesive conforming to AASHTO No. M237, Type 2, or with bituminous adhesive.

X1.3.1 The engineer should be the judge as to when Rapid Set Type adhesive has set sufficiently to bear traffic.

X1.3.2 Regardless of the type of adhesive used, markers should not be placed under the following conditions:

X1.3.2.1 When either the pavement or the air temperature is 0°C (32°F) or less when using rapid set epoxy, 10°C (50°F) or less when using standard set epoxy or 4.4°C (40°F) or less when using bitumen,

X1.3.2.2 If the relative humidity of the air is greater than 80 %,

X1.3.2.3 If the pavement is not surface dry, and

X1.3.2.4 On new asphalt concrete surfacing until the surfacing has been opened to public traffic for a period of not less than 14 days.

X1.3.3 The portion of the highway surface to which the marker is to be bonded by the adhesive should be free of dirt, curing compound, grease, oil, moisture, loose or unsound layers, paint and any other material which would adversely affect the bond of the adhesive. A wire brush should be used, if necessary, to loosen and remove dirt, and the surface should be brushed or blown clean. New portland cement concrete should be blast cleaned. The adhesive should be placed uniformly on the cleaned pavement surface or on the bottom of the marker in a quantity sufficient to result in complete coverage of the area of contact of the marker with no voids present and with a slight excess after the marker has been lightly pressed in place; ideally there will be approximately 0.060 in. adhesive between the marker and the pavement.

X1.3.4 For epoxy installations, excess adhesive around the edge of the marker, excess adhesive on the pavement, and adhesive on the exposed surfaces of the markers should be immediately removed. Soft rags moistened with mineral spirits conforming to Federal Specification TT-T-291 or kerosine may be used, if necessary, to remove adhesive from exposed faces of pavement markers. No other solvent should be used.

X1.3.5 For epoxy installations, the marker should be protected against impact until the adhesive has hardened to the degree designated by the engineer.

X1.3.6 The epoxy adhesive requires that the mixing operation and placing of the markers be done rapidly. When hand mixing the Standard Set Type adhesive, not more than 1 L (1 qt) should be mixed at one time, and the markers should be aligned and pressed into place within 5 min after mixing operations are started. Any mixed batch which becomes so viscous that the adhesive cannot be readily extruded from under the marker on application of slight pressure should not be used. Rapid Set Type adhesive should not be mixed by hand.

X1.3.7 The Rapid Set Type adhesive should be mixed by a 2-component type automatic mixing and extrusion apparatus. When machine mixing the Standard Set Type adhesive, or the Rapid Set Type adhesive, the markers should be placed within 60 s after the adhesive has been mixed and extruded and no further movement of the marker should be allowed. In addition, no more than 90 s should be permitted between the time the adhesive is in place on the roadway and not subject to further movement. The mixed adhesive should not remain in the mixing head for more than 45 s. Adhesive remaining in the mixing head longer than this period should be wasted before resuming the operation.

X1.3.8 Automatic mixing equipment for the epoxy adhesive should use positive displacement pumps and should properly meter the two components in the specified ratio,  $\pm 5\%$  by volume of either component. At the beginning of each day and at any other time ordered by the engineer, the ratio should be checked by the contractor in the presence of the engineer. This check should be made by disconnecting the mixing heads, or using suitable bypass valves, and filling two suitable containers with the unmixed components. The mixing head should properly mix the two components so that there is no trace of black or white streaks in the mixed material.

X1.3.9 Voids in a cured, undisturbed sample of the mixed adhesive obtained from the extrusion nozzle should not exceed 4 %.

X1.3.10 Bituminous adhesive should be dispensed from a thermostatically controlled melter-applicator at a temperature of 141 to 218°C (375 to 425°F). The material should be stirred frequently to ensure even heating. The adhesive should be dispensed in a puddle larger than the bottom of the marker, and the marker should be dropped onto the puddle as quickly as possible, preferably within 5 s of adhesive placement. The marker should be pressed lightly onto the adhesive. The adhesive will set up in approximately 2 min and typically requires no protection from traffic.

*The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).*