



# Standard Practice for Laboratory Preparation of Gelled Vehicles Using a Resin Kettle<sup>1</sup>

This standard is issued under the fixed designation D 5165; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This practice covers a laboratory procedure for the gelation of a resin solution, ink varnish, or vehicle using a resin kettle.

1.2 Guidance in preparing gelled vehicle samples suitable for use in laboratory sample quantity oil-based printing inks is provided.

1.3 The procedure outlined is not intended as a means of rating or evaluating resin or vehicle gelability, and is applicable only if the solutions, varnishes, or vehicles produced are of a rheology that is measurable by conventional ink and varnish industry viscometers.

1.4 The values stated in SI units of measurement are to be regarded as the standard. The values given in parentheses are for information only.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

### 2.1 ASTM Standards:

- D 154 Guide for Testing Varnishes<sup>2</sup>
- D 1545 Test Method for Viscosity of Transparent Liquids by Bubble Time Method<sup>2</sup>
- D 1725 Test Method for Viscosity of Resin Solutions<sup>2</sup>
- D 4040 Test Method for Viscosity of Printing Inks and Vehicles by Falling Rod Viscometer<sup>3</sup>
- E 1 Specifications for ASTM Thermometers<sup>4</sup>

## 3. Terminology

### 3.1 Definitions:

3.1.1 *gel or gelled vehicle*—any resin solution, or a more complex blend of resins and alkyds that has been cooked to build molecular weight or reacted with a gelling or crosslinking

agent (for example, organo-aluminum compounds) and exhibits a pseudoplastic rheology.

3.1.2 *pregel or pregel vehicle*—the resin solution or vehicle components comprising the vehicle prior to the addition of gelling agent and viscosity adjusting solvent.

3.1.2.1 *Discussion*—The terms vehicle and varnish are commonly used interchangeably. Some vehicle and varnish chemists, however, may consider a varnish to be a vehicle that undergoes a chemical reaction during a cooking cycle.

## 4. Summary of Practice

4.1 Prepare a pregel vehicle by dissolving all vehicle, or varnish components, or both, in a heated 1-L, resin kettle with inert gas blanket.

4.2 Add gellant solution into the pregel vehicle. Mix using the suggested stirring rate at the prescribed reaction temperature for 1 h.

4.3 Remove the vehicle from heat. Pour into a 1-qt can and allow the sample to sit overnight before testing.

## 5. Significance and Use

5.1 This practice provides a means of preparing gel vehicles in laboratory equipment that most closely resembles production reactors. It can be used to predict the performance of gel vehicle components (resins, gellants, alkyds, etc) in the user's equipment.

5.2 An ample amount of gel vehicle can be prepared for use in preparing inks for press testing.

## 6. Apparatus (see Fig. 1)

6.1 *Balance or Scale*, weighing to  $\pm 0.1$  g accuracy.

6.2 *Resin Kettle*, 1-L with 5-neck kettle head.

6.3 *Electric Stirrer*, equipped with speed control.

6.4 *Glass Stirring Rod*.

6.5 *Paddle*, 6.4 cm (2.5 in.) in width.

6.6 *Heat Mantle*, to fit 1-L resin kettle.

6.7 *Electron Temperature Control Device*.

6.8 *Thermometer*, with 15.24-cm (6-in.) immersion and a range of 0 to 250°C, conforming to Specification E 1.

6.9 *Inert Gas Blanket Source*, (for example, nitrogen, carbon dioxide).

6.10 *Auxiliary Equipment*, (that is, stopper, Y tube, condenser, bubbler, etc).

<sup>1</sup> This practice is under the jurisdiction of ASTM Committee D-1 on Paint and Related Coatings, Materials, and Applications and is the direct responsibility of Subcommittee D01.37 on Ink Vehicles.

Current edition approved May 15, 1993. Published July 1993.

<sup>2</sup> *Annual Book of ASTM Standards*, Vol 06.03.

<sup>3</sup> *Annual Book of ASTM Standards*, Vol 06.02.

<sup>4</sup> *Annual Book of ASTM Standards*, Vol 14.03.

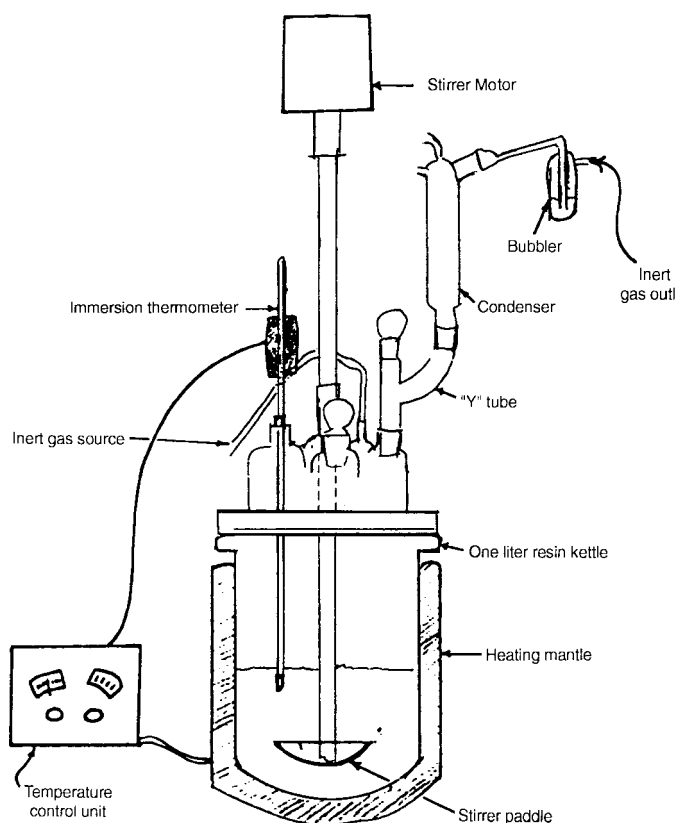


FIG. 1 Gel Vehicle Preparation Apparatus

6.11 Insulated Gloves.

7. Reagents and Materials

7.1 Nonvolatile materials will include resins, alkyds, gellants, etc consistent with those used in the manufacture of lithographic ink vehicles (for example, aromatic hydrocarbon resins, modified rosin ester resins, long oil linseed isophthalic alkyds, and aluminum compounds).

7.2 Solvents used in this procedure will be those most often used in the manufacture of lithographic ink vehicles, for example, hydrocarbon petroleum distillate C12-C16.

8. Procedure

8.1 Weigh pregel solution, vehicle, or varnish components for a 500-g sample into resin kettle.

8.1.1 Pregel system components could include: resin(s), alkyd(s), and solvent(s).

8.1.2 Separately prepare a gellant solution to be added after resin dissolution. Dilute gellant to between 30 and 50 % gellant with the major vehicle solvent.

8.2 Start mixer and be sure that all materials are mixing.

8.3 Start heating mixture to 160°C, under inert gas blanket and refluxing at full power. Record time.

8.4 At 150°C, reduce to approximately ¾ power and continue heating to 160°C.

8.5 When the temperature reaches 160°C, check that all systems components have been dissolved into a homogeneous solution. If yes, record the time and the r/min of the stirrer (if possible). If not, allow system to mix until all components are dissolved.

8.6 After a homogeneous vehicle is obtained, reduce the solution temperature to 120°C.

8.7 Add the desired quantity of gellant solution to the pregel vehicle at a temperature of 120°C or below and mix thoroughly.

8.8 Raise reaction temperature to 160°C (or defined reaction temperature), stirring at 380 to 420 r/min (if able to determine stirring speed), and record time.

8.8.1 Hold at 160°C, or other reaction temperature, for 1 h with constant stirring.

8.9 After 1 h, or the prescribed reaction cycle, discontinue heating.

8.10 Allow kettle to cool to a safe handling temperature; pour gel vehicle into a 1-qt can.

9. Evaluation

9.1 Sample should be tested immediately after preparation and after 24 h to determine the effects of post gelation.

9.2 Guide D 154 outlines many methods applicable to the testing of varnishes. It is an excellent guide for those looking for specific areas of evaluation.

9.3 Lightly gelled resin solutions and vehicles can be tested for changes in viscosity by using either Test Methods D 1545 or D 1725. These test methods both use Gardner bubble tubes to determine the viscosity of liquids.

9.4 Another test method for testing gelled ink vehicles is Test Method D 4040. This test method utilizes a falling-rod viscometer and can be used to determine the non-Newtonian nature of vehicles. The test method gives poor precision, however. Other viscometers used for determining the rheology of gelled vehicles include: variable shear rate viscometers, and cone and plate viscometers.

10. Report

10.1 Report the following information on vehicle preparation:

- 10.1.1 Sample identification,
- 10.1.2 Test run,
- 10.1.3 Starting time of heat-up,
- 10.1.4 Initial stirring rate in r/min,
- 10.1.5 Time at which 160°C is reached,
- 10.1.6 Time at which all pregel material is dissolved,
- 10.1.7 Time at which cooling cycle is initiated,
- 10.1.8 Time at which pregel vehicle reached 120°C or below,
- 10.1.9 Time when gellant solution is added to pregel vehicle,
- 10.1.10 Time when heat up cycle toward 160°C has begun,
- 10.1.11 Time when vehicle temperature reaches 160°C or optimum reaction temperature,
- 10.1.12 Length of time that the reaction is held at 160°C or the optimum reaction temperature, and
- 10.1.13 Time and temperature when gel vehicle is poured for storage.

10.2 A report on gel vehicles properties should contain:

- 10.2.1 Sample identification,
- 10.2.2 Test run, and
- 10.2.3 Results of the analyses made. In the case of falling rod viscometer determinations the following data could be

obtained using Test Method D 4040:

10.2.3.1 Apparent viscosity at 2500/s at 25°C,

10.2.3.2 Pseudo-Bingham Yield value at 25°C,

10.2.3.3 Shortness ratio (yield value/apparent viscosity),  
and

10.2.3.4 Slope (non-Newtonian parameter) as defined in  
Test Method D 4040.

## 11. Keywords

11.1 gel; gelability; gelled varnish; gelled vehicle; non-Newtonian fluid; pregel; pregel varnish; pregel vehicle; slope; viscometer; yield value shortness ratio

*The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, 100 Barr Harbor Drive, West Conshohocken, PA 19428.*