



Standard Test Methods of Testing Cellulose Acetate¹

This standard is issued under the fixed designation D 871; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 These test methods cover procedures for testing cellulose acetate.

1.2 The test procedures appear in the following sections:

	Sections
Ash	8 to 11
Color and Haze	67 to 72
Combined Acetyl or Acetic Acid Content	
Test Method A. Solution Method	17, 19 to 23
Test Method B. Heterogeneous Saponification Method	17, 24 to 26
Free Acidity	12 to 16
Heat Stability	47 to 56
Hydroxyl Content	27 to 33
Intrinsic Viscosity	57 to 62
Moisture Content	4 to 7
Primary Hydroxyl Content	34 to 39
Sulfur or Sulfate Content	40 to 45
Viscosity	63 to 66

This standard does not purport to address the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

2. Referenced Documents

2.1 ASTM Standards:

- D 1193 Specification for Reagent Water²
- D 1343 Test Method for Viscosity of Cellulose Derivatives by Ball-Drop Method³
- D 2929 Test Method for Sulfur Content of Cellulosic Materials by X-Ray Fluorescence³
- D 5897 Test Method for Determination of Percent Hydroxyl on Cellulose Esters by Potentiometric Titration—Alternative Method³

3. Purity of Reagents

3.1 Reagent grade chemicals shall be used in all tests. Unless otherwise indicated, it is intended that all reagents shall conform to the specifications of the Committee on Analytical Reagents of the American Chemical Society, where such

specifications are available.⁴ Other grades may be used, provided it is first ascertained that the reagent is of sufficiently high purity to permit its use without lessening the accuracy of the determination.

3.2 Unless otherwise indicated, references to water shall be understood to mean reagent tared, low, wide-form weighing bottle and water, conforming to Specification D 1193.

MOISTURE CONTENT

4. Significance and Use

4.1 Moisture content of the cellulose ester can be used to estimate the dry weight of the cellulose ester. Since cellulose esters are desiccants, their moisture content can vary greatly depending on storage.

5. Procedure

5.1 Transfer about 5 g of the sample to a tared, low, wide-form weighing bottle and weigh to the nearest 0.001 g. Dry in an oven for 2 h at 105 ± 3 C. Remove the bottle from the oven, cover, cool in a desiccator, and weigh.

6. Calculation

6.1 Calculate the percentage of moisture as follows:

$$\text{Moisture, \%} = (A/B) \times 100$$

where:

A = weight loss on heating, g, and

B = sample used, g.

7. Precision and Bias

7.1 No statement on bias can be made as no reference material is available as a standard.

ASH

8. Significance and Use

8.1 Ash content gives an estimate of the inorganic content of cellulose ester samples. The presence of high levels of inorganic content (ash) can be detrimental to the melt stability

¹ These test methods are under the jurisdiction of ASTM Committee D-1 on Paint and Related Coatings, Materials, and Applications and are the direct responsibility of Subcommittee D01.36 on Cellulose and Cellulose Derivatives.

Current edition approved Nov. 10, 1996. Published January 1997. Originally published as D 871 – 46. Last previous edition D871 – 91.

² *Annual Book of ASTM Standards*, Vol 11.01.

³ *Annual Book of ASTM Standards*, Vol 06.03.

⁴ *Reagent Chemicals, American Chemical Society Specifications*, American Chemical Society, Washington, DC. For suggestions on the testing of reagents not listed by the American Chemical Society, see *Analar Standards for Laboratory Chemicals*, BDH Ltd., Poole, Dorset, U.K., and the *United States Pharmacopoeia and National Formulary*, U.S. Pharmacopoeial Convention, Inc. (USPC), Rockville, MD.

and optical clarity of a cellulose ester in melt processing or act as a potential source of insolubles when the ester is used in solution.

9. Procedure

9.1 Dry the sample for 2 h at $105 \pm 3^\circ\text{C}$ and weigh 10 to 50 g, to the nearest 0.01 to 0.1 g, depending on its ash content and the accuracy desired. An air-dried sample may be used and calculated to dry weight using the value for moisture determined as in Sections 5 and 6. Burn directly over a flame in a 100-mL tared platinum crucible that has been heated to constant weight and weighed to the nearest 0.1 mg. Add the sample in portions if more than 10 g is taken. The sample should burn gently and the portions should be added as the flame subsides. Continue heating with a burner only as long as the residue burns with a flame. Transfer the crucible to a muffle furnace and heat at 550 to 600°C for 3 h, or longer if required, to burn all the carbon. Allow the crucible to cool and then transfer it, while still warm, to a desiccator. When the crucible has cooled to room temperature, weigh accurately to the nearest 0.1 mg.

10. Calculation

10.1 Calculate the percentage of ash as follows:

$$\text{Ash, \%} = (A/B) \times 100$$

where:

A = ash, g, and

B = sample used, g.

11. Precision and Bias

11.1 No statement on bias can be made as no reference material is available as a standard.

FREE ACIDITY

12. Significance and Use

12.1 Free Acidity is a measure of unesterified organic acid in the ester. The presence of high levels of free acid is potentially detrimental to the melt processing of the ester and can impact the odor of the ester.

13. Reagents

13.1 *Phenolphthalein Indicator Solution* (1 g/100 mL)—Dissolve 1 g of phenolphthalein in 100 mL of ethyl alcohol (95 %).

13.2 *Sodium Hydroxide, Standard Solution* (0.01 N)—Prepare and standardize a 0.01 N solution of sodium hydroxide (NaOH).

14. Procedure

14.1 Shake 5 g of the sample, ground to pass a No. 20 (850 μm) sieve and corrected for moisture content if necessary, in a 250-mL Erlenmeyer flask with 150 mL of freshly boiled, cold water. Stopper the flask and allow it to stand for 3 h. Filter off the cellulose acetate and wash it with water. Titrate the combined filtrate and washings with 0.01 N NaOH solution, using phenolphthalein indicator solution.

14.2 Run a blank determination on the water, using the same volume as was used in extracting the sample.

15. Calculation

15.1 Calculate the percentage of acidity as free acetic acid as follows:

$$\text{Free acetic acid, \%} = [(A - B)N \times 0.06 \times 100]/W \quad (1)$$

where:

A = NaOH solution used to titrate the sample, mL,

B = NaOH solution used to titrate the blank, mL,

N = normality of the NaOH solution, and

W = sample used, g.

16. Precision and Bias

16.1 No statement on bias can be made as no reference material is available as a standard.

COMBINED ACETYL OR ACETIC ACID CONTENT

17. Scope

17.1 Two test methods are described for determining the combined acetyl or acetic acid content. The first, described in Sections 19 to 22, is more precise, but less widely applicable, than the method described in Sections 24 to 26.

18. Significance and Use

18.1 Acetyl or acetic acid content is a measure of the amount of acetic acid esterified onto the cellulose backbone of the polymer. The amount of substitution of acetate ester has a very strong effect on the polymer's solubility and physical properties.

Test Method A—Solution Method

19. Apparatus

19.1 *Weighing Bottle*, glass-stoppered, 15-mL capacity, 25-mm diameter by 50-mm high.

19.2 *Tray*, copper or aluminum, approximately 5 $\frac{3}{8}$ in. (136.5 mm) square, containing 25 compartments 1 in. (25.4 mm) square. Each compartment shall have the correct dimensions to contain one weighing bottle. The entire tray shall fit inside a desiccator and should have a basket-type handle to facilitate the introduction and removal of the tray (convenient but not essential).

19.3 *Buret*, automatic zero, 35-mL, 25-mL bulb, stem graduated from 25 to 35 mL in 0.05-mL increments; or pipet, automatic zero, 30-mL, for 1.0 N NaOH solution.

19.4 *Buret*, automatic zero, 15-mL, 10-mL bulb, stem graduated from 10 to 15 mL in 0.05-mL increments, for 1 N H_2SO_4 .

19.5 *Buret*, 5-mL, in 0.01 or 0.1-mL divisions, for back titration with 0.1 N NaOH solution.

19.6 *Magnetic Stirrer*, for single flask.

19.7 *Magnetic Stirrer*, capacity twelve or more flasks.

19.8 *Stirring Bars*, stainless steel Type 416, length 50 mm, diameter 5 to 6 mm, or equivalent, dimensions not critical.

20. Reagents

20.1 *Acetone*—Add one 30-mL portion of 1.0 N NaOH solution to a mixture of 150 mL acetone and 100 mL hot water,

allow to stand with frequent swirling for 30 min, and titrate with 1.0 *N* H₂SO₄. Add another 30-mL portion of 1.0 *N* NaOH solution to 100 mL of hot water, allow to stand for 30 min, and titrate. The difference between the two titrations shall not exceed 0.05 mL.

20.2 *Dimethyl Sulfoxide*.

20.3 *Pyridine*.

20.4 *Sodium Hydroxide Solution* (40 g/L)—Dissolve 40 g of sodium hydroxide (NaOH) in water and dilute to 1 L.

20.5 *Sodium Hydroxide, Standard Solution* (0.1 *N*)—Prepare and standardize a 0.1 *N* solution of NaOH.

20.6 *Sulfuric Acid* (1.0 *N*)—Prepare and standardize a 1.0 *N* solution of sulfuric acid (H₂SO₄).

20.7 *Phenolphthalein Indicator Solution* (1 g/100 mL)—Dissolve 1 g of phenolphthalein in 100 ml of ethyl alcohol (95 %).

21. Procedure

21.1 Dry 1.9 ± 0.05 g of the ground well-mixed sample in a weighing bottle for 2 h at 105 ± 3°C and weigh the dried sample by difference to the nearest 1 mg into a 500-mL wide-mouth Erlenmeyer flask. Prepare a blank by drying approximately 3.8 g of potassium acid phthalate and weighing it by difference into a flask as described. Carry the blank through the entire procedure.

NOTE 1—Potassium acid phthalate is used so that the concentration of the NaOH in contact with the solvent in the blank will be approximately the same as that in contact with the sample and so that the titration of the blank will be approximately the same as the titration of the sample, thus avoiding errors caused by using a different buret for the titration of the blank and the sample or by refilling the 15-mL buret. If desired, however, the potassium acid phthalate may be omitted.

21.2 If the acetyl content is 32 to 41 % or the acetic acid content is 45 to 57 %, put the sample into solution as follows: Add 150 mL of acetone and 5 to 10 mL of water and swirl to mix. Stopper the flask and allow it to stand with occasional swirling until solution is complete. Solution may be hastened by magnetic stirring or by any suitable mechanical shaking that will provide a gentle rocking type of agitation to avoid splashing the solution on the stopper. It is essential that complete solution be effected. Proceed in accordance with 21.4.

21.3 If the acetyl content is 41 to 44.8 % or the acetic acid content is 57 to 62.5 %, dissolve the sample by either of the following two methods:

21.3.1 Gently rotate the flask by hand to distribute and spread the sample in a thin layer over the bottom of the flask. Add 70 mL of acetone to the flask and swirl gently until the sample particles are completely wetted and evenly dispersed. Stopper the flask and allow it to stand undisturbed for 10 min. Carefully add 30 mL of dimethyl sulfoxide from a graduate to the flask, pouring the solvent down the sides of the flask to wash down any sample particles clinging to the side. Stopper the flask and allow it to stand with occasional swirling until solution is complete. Magnetic stirring or gentle mechanical agitation that will not splash the solution is recommended. When solution appears to be complete, add 50 mL of acetone and swirl or stir for 5 min. Proceed in accordance with 21.4.

21.3.2 Dimethyl sulfoxide is the preferred solvent, but if it

is not available, spread the sample in a thin layer over the bottom of the flask, add 15 mL of acetone, swirl to wet the particles with acetone, stopper the flask, and allow the mixture to stand undisturbed for 20 min. Add 75 mL of pyridine without shaking or swirling, and allow to stand for 10 min. Heat the solution just to boiling and swirl or stir for 5 min. Again heat to boiling and swirl or stir for 10 min. Continue to heat and stir until the mixture is homogeneous and all large gel masses are broken down into individual highly swollen particles. When these highly swollen gel particles are well dispersed and are not fused together in large gel masses, no further heating is necessary. Cool the flask, add 30 mL of acetone, and swirl or stir for 5 min. Proceed in accordance with 21.4.

21.4 Add 30 mL of NaOH solution (40 g/L) with constant swirling or stirring to the solution of the sample and also to the blank. Use of a magnetic stirrer is recommended (Note 2). It is absolutely necessary that a finely divided precipitate of regenerated cellulose, free from lumps, be obtained. Stopper the flask and let the mixture stand with occasional swirling, or stir on the magnetic stirring unit. Allow 30 min for saponification of lower acetyl samples, 2 h for high acetyl samples when dimethyl sulfoxide is the solvent, and 3 h when pyridine is the solvent. At the end of the saponification period, add 100 mL of hot water, washing down the sides of the flask, and stir for 1 or 2 min. Add 4 or 5 drops of phenolphthalein indicator solution and titrate the excess NaOH solution with 1.0 *N* H₂SO₄ (Note 3). Titrate rapidly with constant swirling or stirring ring until the end point is reached; then add an excess of 0.2 or 0.3 mL of H₂SO₄. Allow the mixture to stand with occasional stirring or preferably stir on the magnetic stirrer for at least 10 min. Then add 3 drops of phenolphthalein indicator solution to each flask and titrate the small excess of acid with 0.1 *N* NaOH solution to a persistent phenolphthalein end point. Take extreme care to locate this end point; after the sample is titrated to a faint pink end point, swirl the mixture vigorously or place it for a moment on the magnetic stirrer. If the end point fades because of acid soaking from the cellulose, continue the addition of 0.1 *N* NaOH solution until a faint persistent end point remains after vigorous swirling or stirring. Titrate the blank in the same manner as the sample.

NOTE 2—While the amount of magnetic stirring is somewhat optional, such stirring during the entire period of the determination is strongly recommended. Solution is more rapid, titrations are more rapid, and the end point can be approached directly and without a back titration.

NOTE 3—It is important to correct all 1.0 *N* H₂SO₄ buret readings for temperature and buret corrections.

22. Calculation

22.1 Calculate the percentage by weight of acetyl and acetic acid as follows:

$$\begin{aligned} & \text{Acetyl or acetic acid, \%} & (2) \\ & = [(D - C)N_a + (A - B)N_b + P] \times (F/W) \text{ (Note 4)} \\ & P = (GH \times 1000)/204.2 \end{aligned}$$

where:

A = NaOH solution required for titration of the sample, mL,

B = NaOH solution required for titration of the blank, mL,
 N_b = normality of the NaOH solution,
 C = H_2SO_4 required for titration of the sample, mL,
 D = H_2SO_4 required for titration of the blank, mL,
 N_a = normality the H_2SO_4 ,
 F = 4.305 for acetyl and 6.005 for acetic acid,
 P = milliequivalents of potassium acid phthalate,
 G = potassium acid phthalate used, g,
 H = purity factor for potassium acid phthalate, and
 W = sample used, g.

NOTE 4—When equal volumes of alkali or acid are added to samples and blank, these amounts cancel out. Thus only the amounts of each added in the titration enter into the calculations. Use of potassium acid phthalate in the blank is recommended. When it is not used, the term P drops out of the equation.

23. Precision and Bias

23.1 No statement on bias can be made as no reference material is available as a standard.

Test Method B—Heterogeneous Saponification Method

24. Reagents

24.1 *Ethyl Alcohol (75 Volume %)*—Mix 790 mL of Formula 2B, 3A, or 30 denatured ethyl alcohol and 210 mL of water.

24.2 *Hydrochloric Acid (0.5 N)*—Prepare and standardize a 0.5 N solution of hydrochloric acid (HCl).

24.3 *Sodium Hydroxide, Standard Solution (0.5 N)*—Prepare and standardize a 0.5 N solution of sodium hydroxide (NaOH).

25. Procedure

25.1 Grind the sample in a Wiley mill or other suitable grinder so that 100 % will pass a No. 20 (850- μ m). (Grinding may be omitted if the sample has suitable texture.) Dry about 1 g of the sample in a weighing bottle at $105 \pm 3^\circ\text{C}$ for 2 h, stopper, and cool in a desiccator. (An oven with mechanical circulation is to be preferred over a convection-type oven).

25.2 Weigh the bottle containing the sample to the nearest 0.001 g, transfer the sample to a 250-mL Erlenmeyer flask, and weigh the bottle again to the nearest 0.001 g. Handle the bottle with either tongs or a clean dry cloth during these manipulations. Add 40 mL of ethyl alcohol (75 %) to each sample. Include a blank determination with each set of samples and carry the blank determination through the complete procedure, including the back titration.

25.3 Heat the flasks, loosely stoppered, for 30 min at 50 to 60°C . Add 40 mL of 0.5 N NaOH solution to each flask and heat again at 50 to 60°C for 15 min. Stopper the flasks tightly and allow to stand at room temperature for about 48 h. If the acetyl content of the sample is over 43 %, or if the sample is hard and horny, allow to stand for about 72 h. At the end of this time back titrate the excess NaOH with 0.5 N HCl, using phenolphthalein as the indicator. Add an excess of about 1 mL of 0.5 N HCl and allow the NaOH to diffuse from the regenerated cellulose for several hours, or, preferably overnight. The disappearance of the pink color indicates the complete neutralization of the NaOH. Titrate the small excess

of HCl with 0.5 N NaOH solution to a phenolphthalein end point. Extreme care must be taken to locate this end point. After the sample is titrated to a faint pink end point, stopper the flask and shake vigorously. The end point may fade because of acid diffusing from the cellulose. Continue the addition of 0.5 N NaOH solution and shaking until the faint pink end point persists after vigorous shaking of the flask.

26. Calculation

26.1 Calculate the percentage of combined acetyl or acetic acid as follows:

$$\text{acetyl or acetic acid, \%} = [(D - C)N_a + (A - B)N_b] \times (F/W) \quad (3)$$

where:

A = NaOH solution required for titration of the sample, mL,
 B = NaOH solution required for titration of the blank, mL,
 N_b = normality of the NaOH solution,
 C = HCl required for titration of the sample, mL,
 D = HCl required for titration of the blank, mL,
 N_a = normality of the HCl solution,
 F = 4.305 for acetyl or 6.005 for acetic acid, and
 W = sample used, g.

HYDROXYL CONTENT

27. Scope

27.1 This test method is applicable to pyridine-soluble cellulose esters and is especially useful when the hydroxyl content is low. Samples containing plasticizer may be analyzed directly by this test method because the plasticizer is removed during washing of the carbanilate.

27.2 A preferred method is available in Test Method D 5897.

28. Summary of Test Method

28.1 Hydroxyl in cellulose acetate is determined by reaction with phenyl isocyanate in pyridine solution under anhydrous conditions to form the carbanilate derivative. The derivative is then analyzed for its carbanilate content by ultraviolet absorption.

28.2 The acetyl content of cellulose acetates may be calculated provided that the degree of polymerization is not excessively low.

29. Significance and Use

29.1 Hydroxyl content is a measure of the free hydroxyl on the cellulose backbone of the polymer. Hydroxyl content has a strong effect on the polymer's solubility and physical properties. Hydroxyl content also impacts the propensity for this polymer to crosslink with various crosslinking agents.

30. Apparatus

30.1 *Spectrophotometer*, complete with hydrogen light source and a set of four 1.00-cm quartz cells, or an equally suitable apparatus. The wavelength calibration, as checked against a mercury lamp, shall be within the manufacturer's tolerances. As a further check, measure the absorbance of a potassium chromate (K_2CrO_4) solution prepared as follows:

Dissolve 0.0400 g of K_2CrO_4 or 0.0303 g of potassium dichromate $K_2Cr_2O_7$ in 0.05 *N* potassium hydroxide (KOH) solution and dilute to 1 litre in a volumetric flask with 0.05 *N* KOH solution. Using the hydrogen lamp, measure the absorbance at 280 nm of a silica cell filled with the K_2CrO_4 solution and also of the same cell filled with water. The absorbance of the solution minus that of the blank shall be 0.723 ± 0.023 .

30.2 *Bottles*, 4-oz, with screw caps, for washing the samples.

30.3 *Special Reflux Tubes* for the carbanilation, constructed as follows (see Fig. 1): Make a test tube approximately 20 by 150 mm from the outer part of a 24/40 standard-taper ground glass joint by closing the open end in a blast lamp. Draw the tubing on the inner joint to a constriction just above the joint. Cut the glass at that point and seal on a short length of 8-mm tubing to provide a bearing for a glass stirrer. Make a stirrer of 4-mm glass rod with a semicircle at right angles to the shaft at the bottom and small enough to fit into the test tube. When properly constructed this unit acts as an air condenser, thus preventing the loss of solvent by evaporation.

30.4 *Pipet*, serological-type, 5-mL capacity, graduated in 0.1-mL divisions.

30.5 *Büchner Funnel*, of a size accommodating 90-mm filter paper.

30.6 *Automatic Shaker*, with speed regulator mechanism.

30.7 *Electric Oven*, maintained at $105 \pm 3^\circ C$.

30.8 *Oil Bath*, equipped with a rack to hold several of the special reflux tubes. This bath shall be kept between 115 and $120^\circ C$.

31. Reagents

31.1 *Acetone*.

31.2 *Ethyl Alcohol*, denatured, Formula 2B, 3A, or 30.

31.3 *Methylene Chloride-Methyl Alcohol Mixture*—Mix 9 parts by weight of methylene chloride with 1 part of methyl alcohol. This mixture should have an absorbance of less than 0.2 at 280 nm in a 1.00-cm silica cell measured against air. Pure methylene chloride has an absorbance of about 0.05, but the commercial product may have an absorbance as high as 1.00. The methylene chloride and methanol should be selected to have low absorbance; otherwise, they should be redistilled.

31.4 *Phenyl Isocyanate*.

31.5 *Pyridine*, redistilled, low water content, preferably less than 0.05 %.

32. Procedure

32.1 In the following procedure the phenyl isocyanate reagent shall be used under anhydrous conditions. Therefore, the sample, containers, pipet, and all other equipment shall be thoroughly dried.

32.2 Place a 0.5-g sample in a special reflux tube and dry in an electric oven at $105^\circ C$ for 2 h. Remove the tube from the oven, add 5 mL of pyridine, assemble the reflux apparatus complete with glass stirring rod, and place in the 115 to $120^\circ C$ oil bath. Stir occasionally until the sample is completely dissolved. Add 0.5 mL of phenyl isocyanate, stir thoroughly, and reflux in the oil bath for $\frac{1}{2}$ h to complete the reaction. Use 0.1 mL of phenyl isocyanate for each percent of estimated hydroxyl content, but never less than 0.5 mL.

32.3 At the end of the reaction time, remove the sample and dilute it with acetone to the proper viscosity for precipitation. The amount of acetone used to thin the solution is a critical factor in acquiring a good precipitate. Samples having low viscosity require little, if any, dilution. The average sample requires the addition of about an equal volume of acetone. Precipitate the carbanilate by pouring the solution into about 200 mL of ethyl alcohol. The precipitate should be fluffy and white. Sticky precipitates indicate too little dilution. Stir the alcohol vigorously during precipitation. Filter off the precipitate, using paper on a Büchner funnel, with suction applied only as long as is necessary to remove the bulk of the solvent; prolonged suction may cause undesirable clumping together of the precipitate.

32.4 Wash by transferring the precipitate to a 4-oz screw cap bottle containing 75 mL of ethyl alcohol, capping securely, and shaking for $\frac{1}{2}$ h on an automatic shaker at medium speed. Filter the precipitate on the Büchner funnel, pressing out as much liquid as possible with a glass stopper. Repeat the washing and filtering operations twice more. Allow the precipitate to air-dry 1 to 2 h at room temperature with good ventilation or preferably overnight to ensure complete removal of the alcohol. (Samples wet with alcohol may sinter and stick to paper or glass when dried at $105^\circ C$.) Dry the sample at $105^\circ C$ in the oven for 1 h and cool in a desiccator. Small manila envelopes are convenient for drying and cooling the samples.

32.5 Weigh 0.1231 g of the dry precipitate into a 100-mL volumetric flask fitted with a ground-glass stopper. Add 60 to

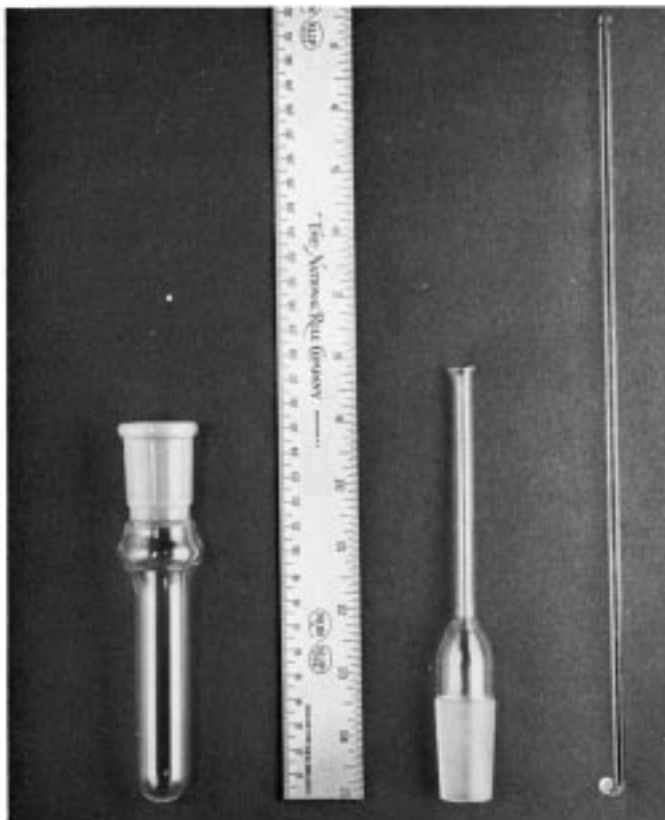


FIG. 1 Special Reflux Tube for Carbanilation

80 mL of the methylene chloride-methyl alcohol mixture, and shake occasionally until complete solution occurs. Dilute to 100 mL and mix thoroughly. Using the spectrophotometer with a 1-cm silica cell measure the absorbance of the solution at 280 nm against the solvent mixture as a reference.

33. Calculation

33.1 Calculate the percentage of carbanilate, c , for a sample weight of 0.1231 g as follows:⁵

$$\text{Carbanilate, \%} = A \times 17.1 \quad (4)$$

where:

A = absorbance.

33.2 Calculate the percentage of hydroxyl as follows:

$$\text{Hydroxyl, \%} = 14.3c / (100 - c)$$

33.3 Calculate the percentage of acetyl as follows:

$$\text{Acetyl, \%} = (4480 - 65.1c) / (100 - c)$$

NOTE 5—The calculation for acetyl content assumes exactly three hydroxyls per anhydroglucose unit and applies to cellulose acetates only.

PRIMARY HYDROXYL CONTENT

34. Summary of Test Method

34.1 The primary hydroxyl content of cellulose acetate is determined by formation of the triphenylmethyl (trityl) ether and measurement of the trityl group by ultraviolet absorbance.⁵ Trityl chloride reacts preferentially with primary hydroxyls. Since there is also a slight reaction with secondary hydroxyls, standardized reaction conditions are important.⁶

35. Apparatus

35.1 See Section 30.

36. Reagents

36.1 *Acetone*.

36.2 *Ethyl Alcohol*, denatured, Formula 2B, 3A, or 30.

36.3 *Methylene Chloride-Methyl Alcohol Mixture*—Mix 9 parts by weight of methylene chloride with 1 part of methyl alcohol. This mixture should have an absorbance of less than 0.2 at 259 nm in a 1-cm silica cell measured against air; otherwise the solvents should be redistilled.

36.4 *Pyridine*, redistilled to a water content less than 0.05 %. The water content may be reduced further by storing over a suitable drying agent, such as a molecular sieve, Type 4A.

36.5 *Trityl Chloride (Chlorotriphenylmethane or Triphenylmethyl Chloride)*, reagent grade.

37. Procedure

37.1 The reagents shall be used under anhydrous conditions. It is imperative that the sample and all equipment be thoroughly dry.

37.2 Place a 0.5-g sample in the test tube of the special reflux apparatus and dry for 2 h at $105 \pm 3^\circ\text{C}$. Add 5 mL of pyridine, insert the top of the reflux apparatus and the stirrer and heat with stirring in a 115 to 120°C oil bath. After the sample has dissolved, add 0.5 g of trityl chloride. If the total hydroxyl content exceeds 3 %, use an additional 0.075 g of trityl chloride for each additional 1 % hydroxyl. Stir the mixture thoroughly and reflux in the oil bath for exactly 2 h at 115 to 120°C . Remove the tube and cool.

37.3 Dilute the sample with acetone to the proper viscosity for precipitation. The amount of acetone used to thin the solution is a critical factor in obtaining a good precipitate. Samples having low viscosity require little, if any, dilution. The average sample requires the addition of about an equal volume of acetone. Precipitate the trityl derivative by pouring the solution into about 200 mL of ethyl alcohol with vigorous stirring. The precipitate should be fluffy and white. Sticky precipitates indicate too little dilution. Separate the precipitate by filtering through paper on a Büchner funnel, with suction applied only as long as necessary to remove the bulk of the solvent; prolonged suction may evaporate the alcohol and cause the precipitate to partially redissolve in the remaining pyridine.

37.4 Wash the precipitate by transferring it to a 4-oz screw cap bottle containing 75 mL of ethyl alcohol, capping securely, and shaking for $\frac{1}{2}$ h on a shaker at medium speed. Again collect the precipitate on a Büchner funnel, pressing out as much liquid as possible with a glass stopper. Repeat this washing and filtering operation twice more, or until the absorbance of the filtrate at 259 nm is about the same as that of an alcohol blank. Allow the precipitate to air-dry on the filter paper for $\frac{1}{2}$ h at room temperature with good ventilation, or preferably overnight, to remove most of the alcohol. (Samples wet with alcohol may sinter or stick to paper or glass when dried at 105°C .) Transfer the sample to a manila envelope, dry it for 1 h at 105°C , and cool in a desiccator.

37.5 Weigh 0.1231 g of the dry trityl ether derivative into a 100-mL volumetric flask fitted with a ground-glass stopper, and dissolve in the methylene chloride-methyl alcohol mixture. Dilute to 100 mL and mix thoroughly. Measure the absorbance of this solution in a 1-cm silica cell using a spectrophotometer at 259 nm against the solvent as a reference.

38. Calculation

38.1 Calculate the trityl content, t , for this concentration of 0.1 g/100 g and with a correction of 0.015 for the absorbance of the cellulose acetate as follows:⁷

$$\text{Trityl, \%} = 25.25 (A - 0.015) \quad (5)$$

where:

A = absorbance.

38.2 Calculate the weight percentage of primary hydroxyl in cellulose acetate as follows:

$$\text{Primary hydroxyl, \%} = 7.02t / (100.4 - t) \quad (6)$$

⁵ Malm, C. J., Tanghe, L. J., Laird, B. C., and Smith, G. C., "Determination of Total and Primary Hydroxyl in Cellulose Esters by Ultraviolet Absorption Methods," *Analytical Chemistry*, ANCHA, Vol 26, 1954, p. 189.

⁶ Malm, C. J., Tanghe, L. J., and Laird, B. C., "Primary Hydroxyl Groups in Hydrolyzed Cellulose Acetate," *Journal of the American Chemical Society*, JACSA, Vol 72, 1950, p. 2674.

⁷ Wagner, R. H., and Russell, John, "Capillary Tube Viscometer for Routine Measurement of Dilute High Polymer Solutions," *Analytical Chemistry*, ANCHA, Vol 20, 1948, pp. 151-157.

38.3 Calculate the percentage primary hydroxyl of the total hydroxyl as follows:

$$\text{Primary hydroxyl of total hydroxyl, \%} = (B/C) \times 100 \quad (7)$$

where:

B = value of primary hydroxyl as determined in 38.2, and

C = value of total hydroxyl as determined in 33.2.

39. Precision and Bias

39.1 No statement on bias can be made as no reference material is available as a standard.

SULFUR OR SULFATE CONTENT

40. Summary of Test Method

40.1 The sulfur or sulfate content of cellulose acetate is measured by oxidizing the sample in a nitric acid-perchloric acid mixture and determining gravimetrically as barium sulfate. To determine combined sulfur the sample must first be reprecipitated into dilute acid to remove noncombined sulfur compounds.

40.2 The sulfur or sulfate content may also be determined by Test Method D 2929. In this case the X-ray method shall be calibrated against the chemical method following in Sections 42 to 45, and the sample shall be treated in accordance with Section 44 if combined sulfur is to be determined.

41. Significance and Use

41.1 Sulfur and sulfate content indicates the amount of sulfur in the cellulose ester either as inorganic salts (usually sulfates) or as organic sulfate (usually as sulfate ester combined to the cellulose backbone). The presence of high levels of sulfur and sulfate can be detrimental to the melt stability of the ester.

42. Apparatus

42.1 *Funnel*, modified by cutting the stem off at the apex of the funnel and fire polishing.

42.2 *Crucibles*, 30-mL, extra-fine porosity.

42.3 *Oven*, controlled at 120 to 125°C.

42.4 *Muffle Furnace*, controlled at $800 \pm 50^\circ\text{C}$.

43. Reagents

43.1 *Acetone*.

43.2 *Acetic Acid (1+49)*—Mix 1 volume of glacial acetic acid with 49 volumes of water.

43.3 *Barium Chloride Solution (100 g/L)*—Dissolve 100 g of barium chloride ($\text{BaCl}_2 \cdot 2\text{H}_2\text{O}$) in water and dilute to 1 L.

43.4 *Hydrochloric Acid (1+1)*—Mix 1 volume of concentrated hydrochloric acid (HCl, sp gr 1.19) with 1 volume of water.

43.5 *Nitric Acid (sp gr 1.42)*—Concentrated nitric acid (HNO_3).

43.6 *Nitric Acid (2+3)*—Mix 2 volumes of concentrated HNO_3 (sp gr 1.42) with 3 volumes of water.

43.7 *Nitric Acid-Perchloric Acid Mixture*—Mix 5 volumes of concentrated HNO_3 with 1 volume of concentrated perchloric acid (HClO_4 , 70 %).

43.8 *Phenolphthalein Indicator Solution (1 g/100 mL)*—Dissolve 1 g of phenolphthalein in 100 mL of ethyl alcohol (95 %).

43.9 *Silver Nitrate Solution (50 g/L)*—Dissolve 50 g of silver nitrate (AgNO_3) in water and dilute to 1 L.

43.10 *Sodium Carbonate (Na_2CO_3)*.

43.11 *Sodium Hydroxide Solution (400 g/L)*—Dissolve 400 g of sodium hydroxide (NaOH) in water and dilute to 1 L.

44. Procedure

44.1 *Treatment Prior to Analysis*—Remove uncombined sulfur as follows (Note 6): Dissolve 25 g of sample in approximately 300 mL of acetone, depending on the viscosity. If the sample is of too high acetyl content to be directly soluble in acetone, cool in a dry ice cabinet overnight; then allow to come to room temperature while tumbling or stirring. Filter the solution, if necessary, through felt or a coarse sintered-glass crucible. Precipitate with rapid stirring into a beaker or pail containing 2 to 3 L of acetic acid (1+49). Filter through a cloth bag or a Büchner funnel and give two 15-min washes with water using mechanical agitation. A little Na_2CO_3 may be added to the last wash to stabilize samples of high sulfur content. Filter and dry overnight at 60°C .

NOTE 6—To analyze for total sulfur content omit this treatment.

44.2 Decomposition:

44.2.1 Weigh 10 ± 0.1 g of cellulose acetate and transfer to a clean, wide-mouth, 500-mL Erlenmeyer flask. Add 50 mL of the HNO_3 - HClO_4 mixture to the flask, and swirl the flask gently to wet the sample thoroughly. Place the modified funnel in the mouth of the flask and heat the flask carefully on a hot plate in a fume hood.

NOTE 7—**Precaution:** Use the utmost care in handling the HNO_3 - HClO_4 mixture. If a spill occurs, wash down with plenty of water. Wear safety glasses or a face shield.

44.2.2 After the mixture becomes hot and less viscous, increase the heat of the hot plate. Continue the digestion until all the sample has been oxidized and the thick reddish-brown fumes of nitrogen dioxide (NO_2) have been expelled. At this point, white fumes will appear and a rather vigorous reaction will occur that is caused by the last traces of organic material being oxidized and the HNO_3 fuming off.

44.2.3 When this reaction starts, remove the flask from the hot plate, swirl gently for a few seconds, and set it on the shelf in front of the hood until the reaction is complete. Place the flask back on the hot plate and continue the digestion until the HClO_4 refluxes about half way up the side of the Erlenmeyer flask and about 5 mL is left in the flask. The HNO_3 - HClO_4 mixture should be clear and colorless. If it is not, set the flask off the hot plate to cool and then add 3 to 5 mL of HNO_3 (sp gr 1.42). Replace the flask on the hot plate and continue heating until the HClO_4 refluxes half way up the flask. Remove the flask from the hot plate and allow the flask and its contents to cool.

44.3 Determination of Barium Sulfate:

44.3.1 Wash the modified funnel top thoroughly with water, collecting the rinsings in the flask. Add 50 mL of water. Swirl the flask to mix the solution thoroughly. Add 2 drops of phenolphthalein indicator solution and neutralize the acid with the NaOH solution to a faint pink. Acidify immediately with HCl (1+1), dropwise, until the solution is just acid to phenolphthalein; then add 2 mL of HCl (1+1).

44.3.2 Filter through a 12.5-cm fine-porosity paper into a clean 400-mL beaker. Wash the flask thoroughly with water, filtering the washings through the paper. Finally wash the paper thoroughly with ten portions of hot water. Dilute the filtrate to approximately 200 mL. Place the beaker on the hot plate and heat almost to boiling. Slowly add 10 mL of BaCl₂ solution from a pipet, stirring the solution during the addition. Do not add the BaCl₂ solution rapidly, as from a graduate, since the rapid addition will produce an impure precipitate. Remove the stirring rod from the beaker and wash it with a stream of water from the wash bottle, collecting the washings in the beaker. Cover the beaker with a watch glass and keep the mixture near the boiling temperature of 6 h or overnight. Do not allow the liquid to evaporate to dryness.

44.3.3 Using suction, decant the supernatant liquid through an extra-fine porosity porcelain filter crucible that has been previously rinsed with acetone, ignited, and weighed to the nearest 0.1 mg. Transfer the precipitate with the aid of a stream of hot water. Always use a stirring rod in this transfer. Scrub the sides and bottom of the beaker with a rubber policeman to remove any adhering precipitate. The crucibles may be used to collect several precipitates one on top of the other. Close control of temperature and time of heating and cooling are necessary. Cleaning with hot water is generally sufficient; drastic attack with cleaning solution should be avoided.

44.3.4 Wash the precipitate on the filter until free of chlorides by the following test: To 5 mL of wash water, collected in a separate test tube or on a watch glass, add 1 mL of HNO₃ (2+3) and 1 mL of AgNO₃ solution. The appearance of a milky white precipitate indicates the presence of chlorides, and the washing should therefore continue until the test is negative. Do not attempt to get a completely negative test for chloride. Discontinue washing when no more than a faint opalescence is produced in the test.

44.3.5 Finally pour a few millilitres of pure acetone through the filter and suck it dry. Place the crucible in a larger crucible or in a metal tray with perforated sides and bottom for protection and place it in an oven at 120 to 125°C for 1 h. Do not handle the crucibles with the fingers between ignition and the completion of weighing; use forceps.

44.3.6 Remove the crucible from the oven and ignite it for 10 min in a muffle furnace at 800 ± 50°C. Cool in a desiccator for 75 ± 15 min and weigh to the nearest 0.0001 g. It is permissible to return the crucible to the oven for at least 15 min before transferring to the desiccator.

44.3.7 From time to time, and especially when using new reagents, run a blank in duplicate in the reagents. If the weight of the precipitate exceeds 0.0005 g, investigate and eliminate the cause. This is equivalent to an error of 0.002 % on a 10-g sample.

45. Calculation

45.1 Calculate the percentage of sulfur and sulfate as follows:

$$\text{Sulfur, \%} = [(C - B) - (E - D)] \times 0.1374 \times 100 / A \quad (8)$$

$$\text{Sulfate, \%} = [(C - B) - (E - D)] \times 0.4115 \times 100 / A \quad (9)$$

where:

<i>A</i>	= weight of sample, g,
<i>B</i>	= weight of crucible for sample, g,
<i>C</i>	= weight of crucible and BaSO ₄ for sample, g,
<i>C - B</i>	= weight of BaSO ₄ for sample, g,
<i>D</i>	= weight of crucible for blank, g,
<i>E</i>	= weight of crucible and BaSO ₄ for blank, g, and
<i>E - D</i>	= weight of BaSO ₄ for blank, g.

46. Precision and Bias

46.1 No statement on bias can be made as no reference material is available as a standard.

HEAT STABILITY

47. Summary of Test Method

47.1 The heat stability of cellulose acetate is one indication of its quality. It is measured by heating the sample for a specified time and temperature, observing it for amount and uniformity of color developed, and possibly also measuring the loss of viscosity as a result of heating. Suggested times of heating are 8 h at 180°C or 2 h at 190°C. The time and temperature of heating, method of grading, and limits are matters for agreement between purchaser and the supplier.

48. Significance and Use

48.1 The heat stability of a cellulose ester is one indication of its quality.

49. Apparatus

49.1 *Heater Block*—A metal block of suitable size is heated electrically and maintained at the specified temperature within ± 1°C. This is best accomplished by providing continuous heat to hold the temperature a few degrees below the specified temperature, and providing intermittent additional heat thermostatically controlled. Holes are drilled in the top of the block to hold test tubes, a thermoregulator, and a thermometer. The block should be insulated.

49.2 *Test Tubes*, either 18 by 150 mm or 20 by 150 mm, fitted with corks. The corks shall be fitted with glass tubes the length of the cork and 4 mm in inside diameter or shall have a small V-shaped notch of equivalent cross-section cut in a vertical position.

50. Solvent

50.1 *Methylene Chloride-Methanol Mixture*—Mix 9 parts by weight of methylene chloride with 1 part of methyl alcohol.

51. Heat Treatment

51.1 Place the sample, ground to pass a No. 20 (850-μm) sieve, in a clean dry test tube and pack it firmly and uniformly. Stopper with a cork having a notch or tube as described in 49.2. Heat the tube and contents for 8 h at 180°C or as otherwise specified.

52. Dry Color Evaluation

52.1 Examine the heated sample for uniformity of color and for the presence of charred or decomposed spots. Compare the color of the material at the bottom of the tube with standards prepared as follows: Heat portions of a check batch of similar

particle size, representative quality and stability, and accepted by mutual agreement between the purchaser and the seller. Pack portions of this check batch firmly in each of twelve clean, dry test tubes and stopper with corks as described in 49.2. Heat the tubes at 180°C, or as otherwise specified, remove one tube each 2 h, and mark the time of heating in hours on each tube. This set of numbered tubes serves as the color standards. They should be checked and renewed if necessary every 6 months.

53. Solution Color Using Platinum - Cobalt Standards

53.1 Heat a 1-g sample for the specified time and temperature and, after cooling, examine for charred or decomposed spots. Dissolve the heated sample in 15 mL of the methylene chloride-methanol mixture. Compare the color of the solution (viewing transversely) with test tubes of platinum-cobalt color standards, prepared as described in Section 70. (It may be necessary to prepare standards having as much as 2000 ppm of platinum for this purpose or to dilute the sample solution before grading.)

54. Solution Color by Spectrophotometer

54.1 The color of the solution prepared as described in Section 53 may also be measured spectrophotometrically. Measure the absorbance at 400 nm against the solvent, using a suitable spectrophotometer with a 1-cm silica cell.

55. Viscosity Change

55.1 Measure the intrinsic viscosity of the heated sample and of an unheated sample as described in Sections 57 to 61 of this test method. The percentage loss of viscosity as the result of heating is a measure of heat stability.

56. Precision and Bias

56.1 No statement on bias can be made as no reference material is available as a standard.

INTRINSIC VISCOSITY

57. Summary of Test Method

57.1 Intrinsic viscosity, expressed in decilitres of solution per gram of solute, is determined by measuring the flow times of a solution of known concentration and also of the solvent used and making a calculation by means of the modified Baker-Philippoff equation.

NOTE 8—By expressing concentration in grams per millilitre rather than grams per decilitre, the result will be limiting viscosity number instead of intrinsic viscosity, and will be 100 times greater.

58. Significance and Use

58.1 Intrinsic viscosity number can be used to estimate the molecular weight of a cellulose ester by using the Mark-Houwink equation and constants measured for the solvent, temperature, and ester of concern.

59. Apparatus

59.1 *Capillary Viscometer*, such as the Wagner apparatus (Fig. 2) or an Ostwald-Fenske-Cannon pipet, that will give a flow time for the solvent of not less than 70 s.

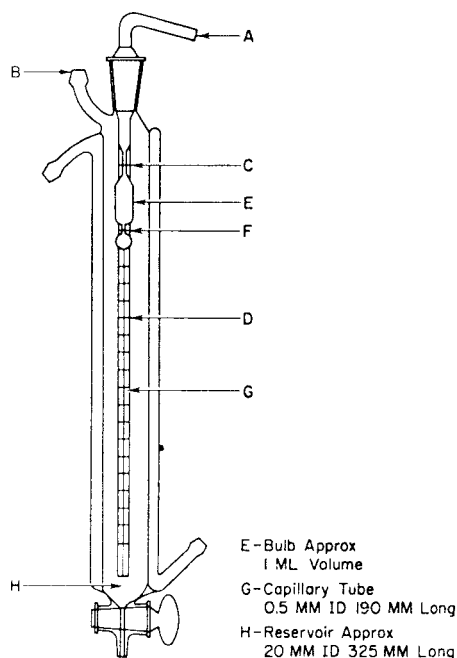


FIG. 2 Wagner Capillary Tube Viscometer⁷

59.2 *Water Bath*—A constant-temperature water bath controlled at 25.0 ± 0.1°C and with a pump for circulating the water through the viscometer jacket or tank.

59.3 *Stop Clock or Watch*, calibrated in tenths of a second.

60. Procedure

60.1 *Sample Preparation*—Dry about 0.26 g of sample in a weighing bottle at 105 ± 3°C for 2 h, stopper, and cool in a desiccator. Weigh the bottle containing the sample to the nearest 0.001 g, transfer the sample to a 250-mL flask, and reweigh the bottle. Pipet into the flask 100 mL of solvent at 25 ± 0.1°C. The solvent used should be mutually agreed upon by the purchaser and the supplier. Suitable solvents are listed in Table 1. After the sample is completely dissolved, place it in the constant-temperature bath at 25°C along with a portion of the solvent used, and allow sufficient time for both to come to

TABLE 1 Solvents for Intrinsic Viscosity Determination

Solvent ^A	Ingredients, weight %	Value of <i>k</i> for Calculation (see 61.2)
A	90 % acetone ^B 10 % ethyl alcohol ^C	10
B	acetone ^B	10
C or D	90 % methylene chloride ^D 10 % ethyl alcohol ^C	3
E	96 % acetone ^B 4 % water	10
F	90 % methylene chloride ^D 10 % methanol ^E	3

^A Solvent designations conform to those used in Table 2 for viscosity determinations.

^B Acetone (99.4 ± 0.1 %) containing 0.3 to 0.5 % water and under 0.3 % ethyl alcohol.

^C Ethyl alcohol (95 volume %). Formula 2B or 3A denatured ethyl alcohol may be used.

^D Methylene chloride having a boiling range of 39.2 to 40.0 C and less than 0.001 % acidity calculated as HCl.

^E Methyl alcohol (sp gr 20/20°C = 0.785 to 0.795).

temperature before making the viscosity measurements. During this conditioning period, water at 25°C should be circulating through the water jacket of the viscometer to allow ample time for the pipet to reach temperature equilibrium.

60.2 *Viscosity Measurements*—Rinse the reservoir and the outside of the capillary tube thoroughly with solvent. Rinse the inside of the capillary tube twice by alternately applying pressure at points *B* and *A* (Fig. 2). Discard the wash portion of the solvent. Pour more solvent into the reservoir and allow several minutes for complete drainage and thermal equilibrium to be obtained. Adjust the outer meniscus to a reference point, *D*, that will give a flow time between 70 and 100 s. Apply air pressure at *B* to force the solvent up through the capillary past the upper timing mark, *C*, on the measuring bulb, *E*. Record the time in seconds required for the meniscus to fall between the timing marks, *C* and *F*. Take a minimum of two readings. Repeat these operations, substituting the solution for the solvent.

61. Calculation

61.1 Calculate the relative viscosity, η_{rel} , as follows:

$$\eta_{rel} = t_1/t_2 \quad (10)$$

where:

t_1 = flow time of solution, and

t_2 = flow time of solvent.

61.2 Calculate the intrinsic viscosity, $[\eta]$, as follows:

$$[\eta] = (k/c) [\text{antilog}(\log \eta_{rel}/k) - 1] \quad (11)$$

where:

k = values from Table 1, and

c = concentration in grams per decilitre (Note 8 in Section 57).

62. Precision and Bias

62.1 No statement on bias can be made as no reference material is available as a standard.

VISCOSITY

63. Significance and Use

63.1 A measurement of viscosity is of great practical utility in determining the proper processing equipment and process concentrations for cellulose esters.

64. Procedure

64.1 *Solution*—Dry the sample for 1 to 2 h at $105 \pm 3^\circ\text{C}$ and cool in a desiccator. Prepare a solution of the dried sample in a solvent and at a concentration mutually agreed upon by the purchaser and the seller. Suitable solutions are listed in Table 2.

64.2 *Viscosity Determination*—Prepare the solution and measure the viscosity in accordance with Test Method D 1343, (Note 10 in Section 71 of these methods).

65. Report

65.1 Report the results in poises, unless otherwise specified. The viscosity values shall be prefixed with the letter A, B, C, etc., corresponding to the formula of the solution employed.

66. Precision and Bias

66.1 No statement on bias can be made as no reference

TABLE 2 Solutions for Viscosity Determination

	Formula					
	A	B	C	D	E	F
	Ingredients, weight %					
Cellulose acetate	20 ^A	20 ^A	20 ^B	15 ^C	20 ^A	10 ^C
Acetone ^D	72	80
Acetone, 96 %
Water, 4 %
Ethyl alcohol ^E	8	...	8	8.5
Methyl alcohol ^F	9
Methylene chloride ^G	72	76.5	...	81
	Typical Solution Densities, g/mL at 25 C					
	0.84	0.86	1.25	1.23	0.86	1.24

^A Acetyl content 40.5 %, max.

^B Acetyl content 40.5 to 42.7 %.

^C Acetyl content 42.7 to 44.8 %.

^D Acetone (99.4 ± 0.1 %) containing 0.3 to 0.5 % water and under 0.3 % ethyl alcohol.

^E Ethyl alcohol (95 volume %). Formula 2B or 3A denatured ethyl alcohol may be used.

^F Methyl alcohol (sp gr 20/20 C = 0.785 to 0.795).

^G Methylene chloride having a boiling range of 39.2 to 40.0°C and less than 0.001 % acidity calculated as HCl.

material is available as a standard.

COLOR AND HAZE

67. Summary of Test Method

67.1 Color and haze determinations on cellulose ester solutions are made by comparison with standards. Simultaneous measurement of these properties is desirable because haze reduces the amount of color observed.

68. Significance and Use

68.1 Solution color and haze of a cellulose ester is a measurement of the optical properties of cellulose esters when dissolved in a specific solvent.

69. Apparatus

69.1 *Light Box*—A suitable light box (Fig. 3 and Fig. 4) is described as follows. The light source consists of a mercury vapor bulb, which requires an auto transformer for the current source. The bulb is mounted horizontally across the lower front


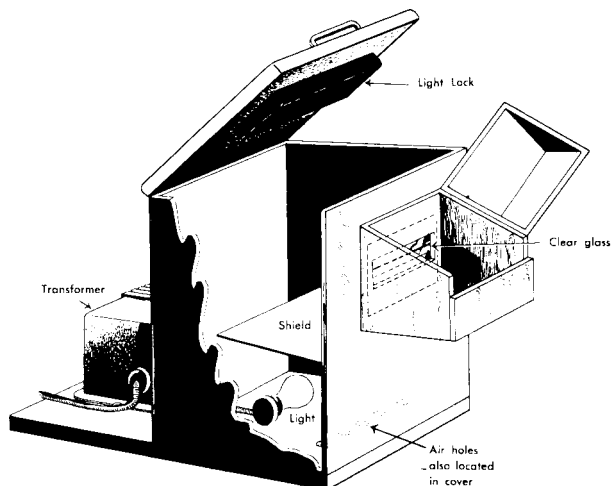


FIG. 3 Color and Haze Apparatus

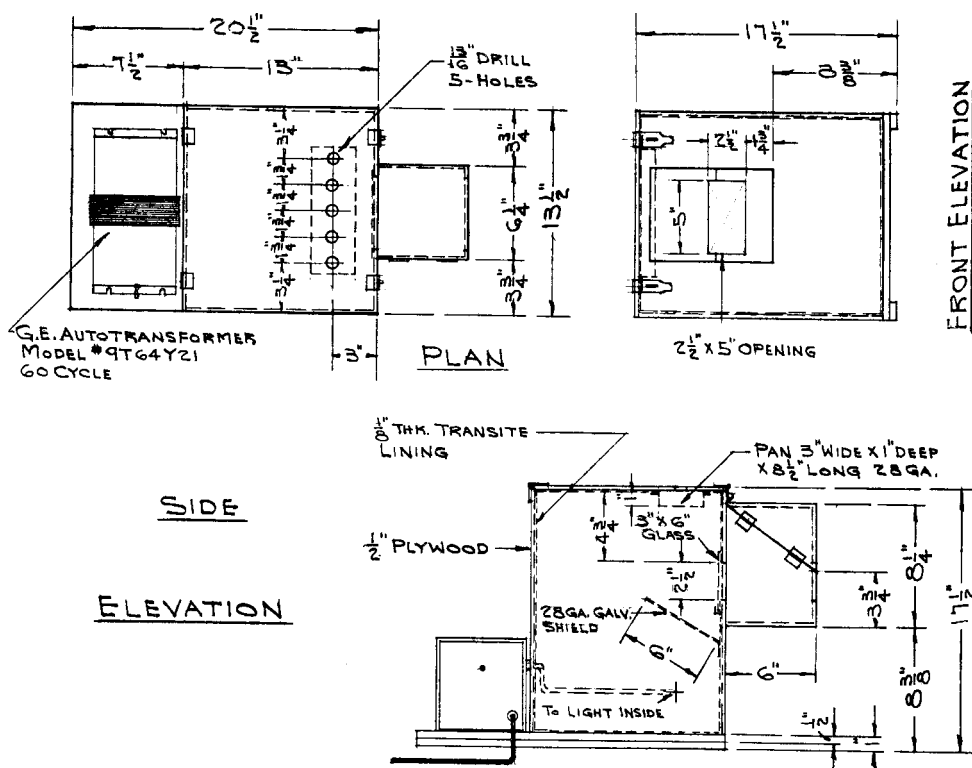

Metric Equivalents

in.	mm	in.	mm	in.	mm	in.	mm	in.	mm
1/8	3.2	1 1/4	44.4	3 3/4	95.2	6 1/4	158.8	8 1/2	215.9
1/2	12.7	2 1/2	63.5	4 3/4	120.6	7 1/2	190.5	13	330.2
1 3/16	20.6	3	76.2	5	127.0	8 1/4	209.6	17 1/2	444.5
1	25.4	3 1/4	82.6	6	152.4	8 3/8	212.7	20 1/2	520.7

FIG. 4 Color and Haze Apparatus (Details)

part of a plywood box 350-mm wide, 430-mm high, and 330-mm deep. This box is lined with a heat resistant board and is painted black inside, except that the inside back surface toward the viewer is white. A bottle holder large enough to hold four bottles is built onto the front of the light box, and a 63.5 by 152.4-mm horizontal viewing hole is cut through the front of the box. This opening is covered with clear glass, and a 6.4-mm strip of black tape is fastened to the glass horizontally to aid in judging haze in the solution. Holes are cut in the bottom and top of the box for cooling by air convection. For continuous use, forced circulation of air would be desirable. A black metal baffle over the bulb prevents direct light on the viewing glass.

69.2 *Sample Bottles*—The bottles used for the sample solutions are French square bottles, 16-oz, with screw caps. These same bottles may be used for the color and haze standards.

NOTE 9—These bottles may also be used for determination of viscosity, as described in 64.2.

69.3 *Cap Liners*—Cap liners shall be of a composition not affected by the solvents used. Liners of fiber board covered with cellophane or aluminum foil are usually satisfactory, but vinyl resin or waxed liners may cause interference with viscosity, color, or haze measurements.

70. Reference Standards

70.1 *Color Standards*—A color standard containing 500 ppm of platinum may be purchased or the solution may also be prepared as follows: Dissolve 1.245 g of potassium platinum chloride (K_2PtCl_6), containing 0.500 g of platinum, and 1.000 g of crystallized cobalt chloride ($CoCl_2 \cdot 6H_2O$), containing 0.248 g of cobalt, in water, add 100 mL of HCl (sp gr 1.19), and dilute to 1 L with water. Prepare standards containing 50, 60, 70, 80, 90, 100, 125, 150, 175, 200, 250, 300, 350, 400 and 500 ppm of platinum by diluting suitable aliquots of the standard solution to 500 mL with water. Place these standards in the special bottles (see 69.2), taking care to select bottles with good clarity and free of flaws. Label and cap tightly.

70.2 *Haze Standards*—Prepare haze standards by diluting a stock solution having a turbidity of 1000 ppm. Prepare bottles containing 10, 20, 30, 40, 50, 60, 70, 80, 90, 100, 125, 150, 175, 200, and 400 ppm of turbidity, label, and cap tightly.

NOTE 10—The previously recommended stock solution for preparing these standards was made from fuller's earth, water, and hydrochloric acid. This solution is no longer available. A comparable stock solution can be made using a diatomaceous earth. To obtain haze levels equivalent to the fuller's earth standard, 1.1 parts diatomaceous should be used in place of 1.0 parts of fuller's earth in preparing the aqueous suspension. No hydrochloric acid is needed.

71. Procedure

71.1 Prepare the solution to be graded by dissolving the cellulose ester in the specified amount and kind of solvent, in one of the square bottles. See Table 2 for suitable solutions. At least 350 mL are required. Tumble until a uniform solution is obtained. Allow the solution to stand until it is free of bubbles before grading it for color and haze:

71.2 Place the bottle containing the solution to be graded at the front of the shelf on the apparatus and place a similar bottle containing water behind it. Place the freshly shaken haze standard at the front of the shelf beside the bottle containing the solution to be tested and place the color standard behind it. Determine the amount of color and haze in the solution by changing the color and haze standards until as good a match as possible has been obtained. The haze standards settle out quickly so they must be reshaken at short intervals. Report results in parts per million for both color and haze.

NOTE 11—When viscosity, color, and haze determinations, and an observation of general appearance are to be made on a cellulose ester sample, a considerable saving in time can be made by using one solution in a square bottle for all three determinations. Dry the cellulose ester as required for the viscosity determination, prepare the solution carefully, and allow the bottle to stand long enough to form a thick solution before tumbling, to avoid solvent loss around the cap. Use a large enough sample to provide at least 350 mL of solution in the bottle. Measure the viscosity as described in Test Method D 1343, and then rate the color and haze.

72. Precision and Bias

72.1 No statement on bias can be made as no reference material is available as a standard.

73. Keywords

73.1 apparent acetyl; ash; cellulose acetate; cellulose ester; color; free acidity; haze; hydroxyl; intrinsic viscosity; sulfate content

The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, 100 Barr Harbor Drive, West Conshohocken, PA 19428.